


ISSN: 1411-9420 (print); 2460-1578 (online)

Indonesian Journal of Chemistry

Vol. 17, No. 2, July 2017

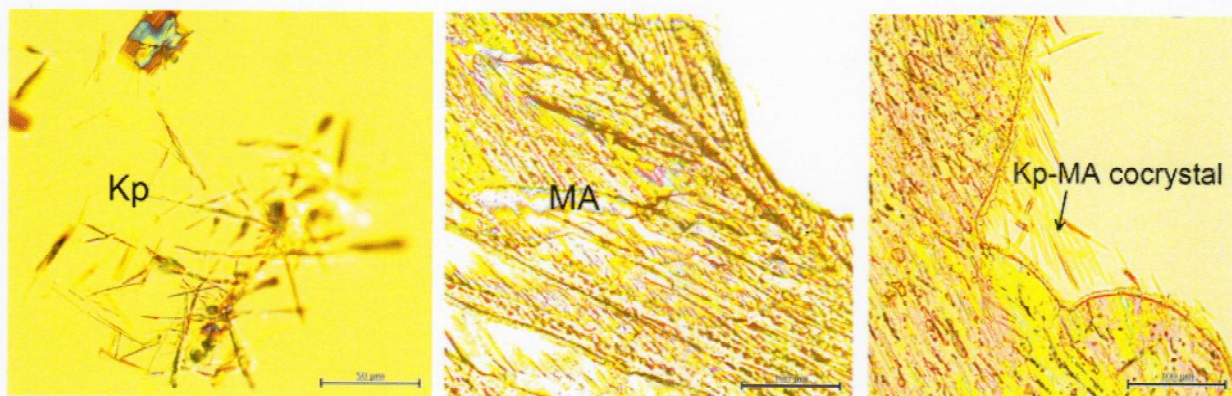

Accredited by DIKTI
No : 58/DIKTI/Kep/2013

Indones. J. Chem.

Vol. 17

No. 2

PP 161-342

Yogyakarta
July 2017

ISSN: 1411-9420 (print)
2460-1578 (online)

Editor in Chief

Prof. Dr.rer.nat. Nuryono, M.S. Email: nuryono_mipa@ugm.ac.id
Department of Chemistry, Universitas Gadjah Mada
Sekip Utara, Yogyakarta Indonesia 55281, Tel/Fax (0062-274)-545188
Website : <https://jurnal.ugm.ac.id/ijc>
Email : ijc@ugm.ac.id or ijcugm@yahoo.com

Vice Editor in Chief

Prof. Dr. Mudasir, M.Eng. Email: mudasir@ugm.ac.id or m_mudasir@hotmail.com

Editorial Board

Prof. Dr. Karna Wijaya, M.Eng. (*Material/Physical Chemistry*)
Dr. Tri Joko Raharjo, M.Si. (*Biochemistry/Bioanalysis*)
Dr. Nurul Hidayat Aprilita, M.Si. (*Analytical/Environmental Chemistry*)
Dr. Dwi Siswanta, M.Eng. (*Analytical/Chemical Sensor*)
Dr. Ria Armunanto, M.Si. (*Computational/Physical Chemistry*)
Dr. Tutik Dwi Wahyuningsih, M.Si. (*Organic/Heterocyclic Chemistry*)
Dr. Akhmad Syoufian (*Material/Physical Chemistry*)
Drs. Iqmal Tahir, M.Si. (*Computational/Physical Chemistry*)

Advisory Editorial Board

Prof. Dr. Hc. Bernd M Rode (University of Innsbruck, Austria)	Dr. Muhamad Abdulkadir Martoprawiro (Bandung Institute of Technology, Indonesia)
Prof. Dr. David. St. C. Black (University of New South Wales, Australia)	Prof. Dr. Hardjono Sastrohamidjojo (Universitas Gadjah Mada, Indonesia)
Prof. Dr. Max Lu (University of Queensland, Australia)	Prof. Dr. Harno Dwi Pranowo, M.Si. (Universitas Gadjah Mada, Indonesia)
Prof. Dr. Naoki Yoshioka (Keio University, Japan)	Prof. Dr. Triyono, SU (Universitas Gadjah Mada Indonesia)
Assoc. Prof. Dr. Wan Ahmad Kamil Mahmood (University Sains Malaysia)	Dr. Sutarno, M.Si. (Universitas Gadjah Mada, Indonesia)
Prof. Kulkarni Shrikant Raghunath (Vishwakarma Institute of Technology, Pune-India)	Prof. Dr. Endang Tri Wahyuni, MS (Universitas Gadjah Mada, Indonesia)
Assoc. Prof. Dr. Abd El Hamid Bensafi (Abou Bekr Belkaid University of Tlemcen, Algeria)	Prof. Dr. Wega Trisunaryanti, M.S., Ph.D. Eng. (Universitas Gadjah Mada, Indonesia)
Dr. Fardad Koohyar (Islamic Azad University, Iran)	Prof. Drs. Jumina, Ph.D. (Universitas Gadjah Mada Indonesia)
Shuai Nie, Ph.D. (Quanterix Corp, Boston, USA)	Dr. Winarto Haryadi, M.Si. (Universitas Gadjah Mada Indonesia)
Prof. Dr. Buchori (Bandung Institute of Technology, Indonesia)	
Prof. Dr. Buhani, M.S. (Lampung University, Indonesia)	

Administrator

Robby Noor Cahyono, S.Si., M.Sc.	Djoko Prihandono
Nurzanah Hidayanti, A.Md.	Ika Prasetyani, A.Md.

Aims and Scope

Indonesian Journal of Chemistry is an international journal covering all aspects of Chemistry, including Chemical Education and Chemical Engineering. The journal publishes original research papers, short communications, and review articles, and has been indexed by SCOPUS since 2012. The paper published in this journal implies that the work described has not been, and will not be published elsewhere, except in abstract, as part of a lecture, review or academic thesis.

Indonesian Journal of Chemistry (ISSN 1411-9420) is published by the Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Gadjah Mada, Sekip Utara, Yogyakarta, Indonesia. All orders accompanied by payment should be sent directly to The Department of Chemistry, Universitas Gadjah Mada. Annual subscription rate is IDR 500,000.00. Reprint order price is IDR 200,000.00 per article. Customers may make payments by transfer on **BNI 46 Universitas Gadjah Mada (Nurzanah Hidayati, Account Nr. 049-598-406-7, SWIFT code: BNINIDJAUGM).**



Menu

[HOME](#) [ABOUT](#) [LOGIN](#) [REGISTER](#) [SEARCH](#) [CURRENT](#) [ARCHIVES](#) [ANNOUNCEMENTS](#)
[Home](#) > [Archives](#) > **Vol 17, No 2 (2017)**

Vol 17, No 2 (2017)

Accredited by DIKTI No : 58/DIKTI/Kep/2013

Date : 22 August 2013

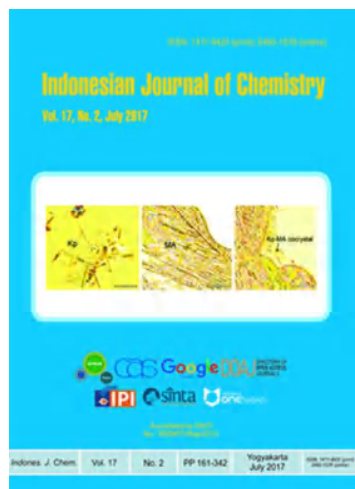


Table of Contents

Articles

- | | |
|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------|
| Formation of Ketoprofen-Malonic Acid Cocrystal by Solvent Evaporation Method
Yudi Wicaksono, Dwi Setyawan, Siswandono Siswandono
10.22146/ijc.24884 Abstract views : 647 views : 443 | 161-166 |
| Validation of a Non-Specific Dye Real-Time PCR Assay for Porcine Adulteration in Meatball Using ND5 Primer
Tri Joko Raharjo, Ery Nourika Alfiraza, Esti Enjelina, Deni Pranowo
10.22146/ijc.22646 Abstract views : 178 views : 355 | 167-174 |
| Performance Test of K₀-NAA and Relative Method for Analysis of Al, Mg, K Nuclides in SRM Lake Sediment Sample
Sunardi Sunardi, Darsono Darsono
10.22146/ijc.24187 Abstract views : 108 views : 239 | 175-181 |
| Characteristics of Fresh Fruit Bunch Yield and the Physicochemical Qualities of Palm Oil during Storage in North Sumatra, Indonesia
Mohammad Basyuni, Nofrizal Amri, Lollie Agustina Pancawaraswati Putri, Indra Syahputra, Deni Arifiyanto
10.22146/ijc.24910 Abstract views : 416 views : 883 | 182-190 |
| Supramolecular Phosphorescent Trinuclear Copper(I) Pyrazolate Complexes for Vapochromic Chemosensors of Ethanol
Hendrik Oktendy Lintang, Nur Fatiha Ghazalli, Leny Yulianti
10.22146/ijc.22553 Abstract views : 192 views : 258 | 191-202 |
| Removal of Sulphate and Manganese on Synthetic Wastewater in Sulphate Reducing Bioreactor Using Indonesian Natural Zeolite
Endah Retnaningrum, Wahyu Wilopo
10.22146/ijc.22710 Abstract views : 172 views : 208 | 203-210 |
| Technique of Batch Adsorption for the Elimination of (Malachite Green) Dye from Industrial Waste Water by Exploitation Walnut Shells as Sorbent
Luma Ahmed Mohammed Ali, Ahmed Saleh Farhood, Firas Fadhel Ali
10.22146/ijc.23063 Abstract views : 191 views : 209 | 211-218 |
| Effect of Anodizing Time and Annealing Temperature on Photoelectrochemical Properties of Anodized TiO₂ Nanotube for Corrosion Prevention Application
Misriyani Misriyani, Abdul Wahid Wahab, Paulina Taba, Jarnuzi Gunlazuardi
10.22146/ijc.24183 Abstract views : 246 views : 258 | 219-227 |
| Comparison of NAA XRF and ICP-OES Methods on Analysis of Heavy Metals in Coals and Combustion Residues | 228-237 |

Focus & Scope

[Author Guidelines](#)
[Author Fees](#)
[Online Submission](#)
[Publication Ethics](#)
[Editorial Board](#)
[Peer Reviewers](#)
[Order Journal](#)
[Visitor Statistics](#)

ARTICLE IN PRESS

List of the accepted articles for future issues.

JOURNAL RANK

Scimago journal rank :



USER

 Username

 Password
 Remember me

NOTIFICATIONS

 View

 Subscribe

JOURNAL CONTENT

 Search

Search Scope

Browse

 By Issue

 By Author

 By Title

 Other Journals

CURRENT ISSUE

 ATOM 1.0

 RSS 2.0

 RSS 1.0

KEYWORDS

 DPPH Pb(II) adsorption
 antibacterial antioxidant biodiesel
 carboxymethyl chitosan catalyst

Resiues

Agus Taftazani, Roto Roto, Novitasari Restu Ananda, Sri Murniasih

 10.22146/ijc.17686  Abstract views : 240 |  views : 277

Styrene and Azo-Styrene Based Colorimetric Sensors for Highly Selective Detection of Cyanide

Agustina Eka Prestiani, Bambang Purwono

 10.22146/ijc.24887  Abstract views : 213 |  views : 215

Home-Made Micro Valve for Determining Malachite Green Dye by Flow Injection Analysis

Amal Saadon Majeed, Ahmed Saleh Farhood, Luma Ahmed Mohammed Ali, Dakhil Nassir Taha

 10.22146/ijc.24707  Abstract views : 79 |  views : 152

Coating of L-Arginine Modified Silica on Magnetite through Two Different Sol-Gel Routes

Amaria Amaria, Suyanta Suyanta, Nuryono Nuryono

 10.22146/ijc.22521  Abstract views : 181 |  views : 209

Modification of Silica Coated on Iron Sand Magnetic Material with Chitosan for Adsorption of Au(III)

Muflikhah Muflikhah, Bambang Rusdiarso, Edy Giri Rachman Putra, Nuryono Nuryono

 10.22146/ijc.22549  Abstract views : 247 |  views : 299

Humic Acid Coated Fe₃O₄ Nanoparticle for Phenol Sorption

Soerja Koesnarjadi, Sri Juari Santosa, Dwi Siswanta, Bambang Rusdiarso

 10.22146/ijc.22545  Abstract views : 244 |  views : 356

Cobalt Oxide-Modified Titanium Dioxide Nanoparticle Photocatalyst for Degradation of 2,4-Dichlorophenoxyacetic Acid

Leny Yuliaty, Nur Azmina Roslan, Wai Ruu Siah, Hendrik Oktendy Lintang

 10.22146/ijc.22624  Abstract views : 243 |  views : 167


The Optimum Conditions of Carboxymethyl Chitosan Synthesis on Drug Delivery Application and Its Release of Kinetics Study

Parsaoran Siahaan, Nadira Cahyaning Mentari, Ustera Octovindra Wiedyanto, Dwi Hudiayanti, Suci Zulaikha Hildayani, Marilyn Dian Laksitorini

 10.22146/ijc.24252  Abstract views : 313 |  views : 302

Synthesis of 1,4-Dioxaspiro[4.4] and 1,4-Dioxaspiro[4.5] Novel Compounds from Oleic Acid as Potential Biolubricant

Yehezkiel Steven Kurniawan, Yudha Ramanda, Kevin Thomas, Hendra Hendra, Tutik Dwi Wahyuningsih

 10.22146/ijc.24891  Abstract views : 153 |  views : 208




Esterification of Crude Palm Oil Using H₂SO₄ and Transesterification Using CaO Catalyst Derived from *Anadara granosa*

Nurhayati Nurhayati, Sofia Anita, Tengku Ariful Amri, Amilia Linggawati

 10.22146/ijc.24909  Abstract views : 211 |  views : 366

Production of Biodiesel from Seed Oil of Nyamplung (*Calophyllum inophyllum*) by Al-MCM-41 and Its Performance in Diesel Engine

Hendro Juwono, Triyono Triyono, Sutarno Sutarno, Endang Tri Wahyuni, Ita Ulfan, Fredy Kurniawan

 10.22146/ijc.24180  Abstract views : 255 |  views : 293

Binary Quantitative Structure-Activity Relationship Analysis to Increase the Predictive Ability of Structure-Based Virtual Screening Campaigns Targeting Cyclooxygenase-2

Enade Perdana Istyastono

 10.22146/ijc.24172  Abstract views : 146 |  views : 224

Synthesis, Characterization and DFT Study of 4,4'-Oxydianiline Imines as Precursors of Tetrahalo-1,3-oxazepine-1,5-dione

Abdullah Hussein Kshash, Mohammed Ghannam Mokhlef

 10.22146/ijc.22437  Abstract views : 164 |  views : 255

Note

Microwave-Assisted Organic Reactions: Eco-friendly Synthesis of Dibenzylidenecyclohexanone Derivatives via Crossed Aldol Condensation

Sri Handayani, Cornelia Budimarwanti, Winarto Haryadi

 10.22146/ijc.25460  Abstract views : 217 |  views : 351



View The Statistics of Indones. J. Chem.

Carboxymethyl Chitosan Catalysts

chitosan eugenol extraction
gamma irradiation immobilization
kinetics magnetite molecular docking
silica synthesis transesterification
voltammetry zeolite

▶ p-ISSN : 1411-9420

▶ e-ISSN : 2460-1578

238-247

248-255

256-263

264-273

274-283

284-290

291-300

301-308

309-315

316-321

322-329

330-335

336-341

LAMPIRAN
 KEPUTUSAN DIREKTUR JENDERAL PENDIDIKAN TINGGI
 NOMOR : 58/DIKTI/Kep/2013
 TANGGAL : 22 Agustus 2013

HASIL AKREDITASI TERBITAN BERKALA ILMIAH PERIODE I TAHUN 2013

Bidang Ilmu	No	Nama Terbitan Berkala Ilmiah	ISSN	Penerbit	Laman	Rekomendasi	Peringkat
Agama	1	Journal of Indonesian Islam	1978-6301	Lembaga Studi Agama & Sosial kerjasama dengan Program Pascasarjana (PPs) IAIN Sunan Ampel Surabaya	http://jiis.sunan-ampel.ac.id/	Terakreditasi	A
	2	Al- Ulum	1412-0534	Lembaga Penerbitan (Lemlit) IAIN Sultan Amai Gorontalo	www.iaingorontalo.ac.id/alulum	Terakreditasi	B
	3	TSAQAFAH (Jurnal Peradaban Islam)	1411-0334	Intitut Studi Islam Darussalam (ISID) Gontor	http://tsaqafah.isid.gontor.ac.id/	Terakreditasi	B
Ekonomi	1	Gajah Mada International Journal Of Business	1411-1128	Master of Management, Fakultas Ekonomika dan Bisnis UGM	http://www.gamajb.mmugm.ac.id/	Terakreditasi	B
Hukum	1	Jurnal Dinamika Hukum	1410-0797	Fakultas Hukum UNSOED	http://www.dinamiclaw.org	Terakreditasi	B
	2	Mimbar Hukum	0852-100X	Fakultas Hukum UGM	http://www.mimbar.hukum.ugm.ac.id	Terakreditasi	B
Kesehatan	1	Universa Medicina	1907-3062	Fakultas Kedokteran Universitas Trisakti	http://univmed.org	Terakreditasi	B
	2	Majalah Kedokteran Bandung	0126-074X	Fakultas Kedokteran Universitas Padjadjaran	www.mkb-online.org	Terakreditasi	B
	3	Jurnal Ners	1858-3598	Program Studi Ilmu Keperawatan Fak. Keperawatan bekerjasama dengan Persatuan Perawat Nasional Indonesia Propinsi Jawa Timur	http://journal.unair.ac.id	Terakreditasi	B
	4	Journal of Indonesian Medical Association (JInMA)/Majalah Kedokteran Indonesia (MKI)	2089-1067	Yayasan Penerbitan Ikatan Dokter Indonesia (YPIDI)	http://indonesiaindonesiamedicaljournal.org/index.php/idmed/issue/archive	Terakreditasi	B
	5	Oto Rhino Laryngologica Indonesiana	0216-3667	Perhimpunan Dokter Spesialis Telinga Hidung dan Tenggorok Bedah Kepala Leher Indonesia	http://www.orli.or.id	Terakreditasi	B

Bidang Ilmu	No	Nama Terbitan Berkala Ilmiah	ISSN	Penerbit	Laman	Rekomendasi	Peringkat
	6	Medical Journal of Indonesia	0853-1773	Fakultas Kedokteran UI	http://mji.ui.ac.id	Terakreditasi	B
	7	Majalah Obstetri & Ginekologi	0854-0381	Departemen Obstetri & Ginekologi Fakultas kedokteran Universitas Airlangga RSUD Dr. Soetomo, Surabaya	http://journal.unair.ac.id	Terakreditasi	B
MIPA	1	Majalah Farmasi Indonesia (Indonesian Journal of Pharmacy)	0126-1037	Fakultas Farmasi UGM	http://www.indonesianjpharm.com	Terakreditasi	B
	2	Indonesian Journal Of Chemistry	1411-9420	Jurusan Kimia FMIPA UGM	http://ijc.chemistry.ugm.ac.id	Terakreditasi	B
	3	Indonesian Journal of Biotechnology	0853-8654	Sekolah Pascasarjana UGM dan Pusat Studi Biotechnologi UGM Yogyakarta	http://ijbiotech.ugm.ac.id	Terakreditasi	B
	4	Journal of the Indonesian Mathematical Society (JIMS)	2086-8952	Himpunan Matematika Indonesia (The Indonesian Mathematical Society/IndoMS)	http://www.jims-a.org	Terakreditasi	B
	5	Makara Seri Sains	1693-6671	Universitas Indonesia	http://journal.ui.ac.id	Terakreditasi	B
Pendidikan	1	SOSIOHUMANIKA: Jurnal Pendidikan Sains Sosial dan Kemanusiaan	1979-0112	Asosiasi Sarjana Pendidikan Sejarah Indonesia (ASPENSI)	www.sosiohumanika-jpsk.com	Terakreditasi	B
Pertanian	1	Jurnal Tanah Tropika (Journal of Tropical Soils)	0852-257X	Jur. Ilmu Tanah Fak. Pertanian UNILA dan Himpunan Ilmu Tanah Indonesia (HITI) Komda Lampung	http://journal.unila.ac.id/index.php/tropicalsoil	Terakreditasi	B
Rekayasa	1	TELKOMNIKA	1693-6930	Universitas Ahmad Dahlan (UAD) dan Institute Of Advanced Engineering and Science (IAES)	http://telkomnika.ee.uad.ac.id	Terakreditasi	A
Seni	1	Mudra (Jurnal Seni Budaya)	0854-3461	UPT. Penerbitan Institut Seni Indonesia Denpasar	http://jurnal.isi-dps.ac.id	Terakreditasi	B
Sosial Humaniora	1	Journal of Government and Politics	1907-8374	Jurusan Ilmu Pemerintahan Universitas Muhammadiyah (ADIPSI) dan (APSPA)	http://jgp.umy.ac.id/	Terakreditasi	B

Bidang Ilmu	No	Nama Terbitan Berkala Ilmiah	ISSN	Penerbit	Laman	Rekomendasi	Peringkat
	2	Jurnal Komunitas	2086-5465	Jurusan Sosiologi dan Antropologi FIS UNNES	http://journal.unnes.ac.id/nju/index.php/komunitas	Terakreditasi	B

Keterangan:

Terakreditasi >85 A (Sangat Baik)

70-85 B (Baik)

Cobalt Oxide-Modified Titanium Dioxide Nanoparticle Photocatalyst for Degradation of 2,4-Dichlorophenoxyacetic Acid

Leny Yuliati^{1,2,3,*}, Nur Azmina Roslan³, Wai Ruu Siah³, and Hendrik Oktendy Lintang^{1,2,3}

¹Ma Chung Research Center for Photosynthetic Pigments, Universitas Ma Chung, Malang 65151, East Java, Indonesia

²Department of Chemistry, Faculty of Science and Technology, Universitas Ma Chung, Malang 65151, East Java, Indonesia

³Centre for Sustainable Nanomaterials, Ibnu Sina Institute for Scientific and Industrial Research, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia

Received February 28, 2017; Accepted July 12, 2017

ABSTRACT

2,4-dichlorophenoxyacetic acid (2,4-D) has been recognized as a possibly carcinogenic compound to human, therefore, 2,4-D should be treated before it is discharged to the environment. Photocatalytic degradation of 2,4-D has been proposed as one of the best methods that offer environmentally safe process. In the present research, titanium dioxide (TiO₂) was modified with cobalt oxide (CoO) and tested for photocatalytic degradation of 2,4-D under UV light irradiation. Different amounts of CoO (0.1, 0.5, 1 and 5 mol%) were added onto TiO₂ by an impregnation method. The photocatalytic reaction was monitored and analyzed by measurement of 2,4-D absorbance using UV spectrophotometer. After 1 h photocatalytic reaction, it was confirmed that the sample with low loading of 0.1 mol% gave the highest photocatalytic activity among the bare and modified TiO₂ photocatalysts. The photocatalytic activity was decreased with the increase of CoO loading, suggesting that the optimum amount of CoO was an important factor to improve the performance of TiO₂. Based on fluorescence spectroscopy, such addition of CoO resulted in the reduced emission intensity, which showed the successful decrease in the electron-hole recombination.

Keywords: 2,4-D herbicide; UV light; titanium dioxide; cobalt oxide; photocatalyst

ABSTRAK

Asam 2,4-diklorofenoksiasetat (2,4-D) telah dikenali sebagai senyawa yang mungkin bersifat karsinogenik pada manusia, oleh karena itu, 2,4-D harus ditangani sebelum dibuang ke lingkungan. Degradasi 2,4-D secara fotokatalitik telah diusulkan sebagai salah satu metode terbaik yang menawarkan proses yang aman terhadap lingkungan. Dalam penelitian ini, titanium dioksida (TiO₂) telah dimodifikasi dengan kobalt oksida (CoO) dan diuji untuk degradasi 2,4-D secara fotokatalitik di bawah iradiasi sinar UV. Kobalt oksida dengan jumlah yang berbeda (0,1, 0,5, 1 dan 5 mol%) telah ditambahkan ke TiO₂ dengan metode impregnasi. Reaksi fotokatalitik dipantau dan dianalisis dengan pengukuran absorbansi 2,4-D menggunakan spektrofotometer UV. Setelah reaksi fotokatalitik selama 1 jam, sampel dengan jumlah rendah yaitu 0,1% mol memberikan aktivitas fotokatalitik tertinggi di antara TiO₂ dan fotokatalis lain yang telah dimodifikasi. Aktivitas fotokatalitik menurun dengan meningkatnya jumlah muatan CoO, menunjukkan bahwa jumlah optimal dari CoO merupakan satu faktor penting untuk meningkatkan kinerja TiO₂. Berdasarkan spektroskopi fluoresensi, penambahan CoO tersebut menghasilkan pengurangan intensitas emisi yang menunjukkan keberhasilan dalam mengurangi rekombinasi elektron-lubang.

Kata Kunci: herbisida 2,4-D; sinar UV; titanium dioksida; kobalt oksida; fotokatalis

INTRODUCTION

2,4-dichlorophenoxyacetic acid (2,4-D) is a common herbicide that has been used for control of broadleaf weeds, which compete with crop production such as wheat and corn, and widely applied to improve grass production by reducing weed competition in

pastureland, lawn, recreational lakes, turf, and roadsides. Owing to its excessive use, these herbicides that contained 2,4-D can cause contamination over agricultural land and water bodies. While the toxicity of the 2,4-D herbicide to human health is continually reviewed and debated, a recent review showed that there is no convincing or consistent evidence for any

* Corresponding author.
Email address : leny.yuliati@machung.ac.id

chronic adverse effect of 2,4-D in humans due to different sample size, imprecise results and misclassification [1]. Even though the inconsistent data were reported, several studies showed significant associations of 2,4-D to cancer, reproductive toxicity, genotoxicity, and neurotoxicity, which could not be neglected. Therefore, the efficient treatment to remove 2,4-D in water still needs to be investigated. There are various methods that have been reported to degrade 2,4-D. One of the most promising methods is by photocatalytic reaction [2-14].

Photocatalytic removal of organic pollutants from water has been a topic of great interest over the years, in which titanium dioxide (TiO_2) and its modifications were mostly reported as the photocatalysts [15-18]. As for photocatalytic degradation of 2,4-D, the most widely used photocatalysts were also TiO_2 and its modifications [2-11]. As a photocatalyst, TiO_2 has a range of useful features, including high photocatalytic activity, stability, low toxicity, ready availability and low cost. Hence, there have been a great number of studies on the preparation, characterization and photocatalytic activities of TiO_2 based photocatalysts. Some strategies have been developed in order to improve the photocatalytic activity of the TiO_2 for degradation of 2,4-D. It was reported that the activity of commercial TiO_2 for degradation of 2,4-D was improved by binding together the pre-calcined TiO_2 in an aqueous sol of TiO_2 nanoparticles with the assistance of chitosan [2]. The activity of TiO_2 for 2,4-D degradation was also enhanced with the addition of reduced graphene oxide and CuInS_2 [3] or Ag/reduced graphene oxide [4]. One of the reasons for higher activity on the modified TiO_2 was proposed to be caused by the higher charge separation of the TiO_2 after the modifications [3-4].

Another approach to improve the activity of TiO_2 photocatalyst for degradation of 2,4-D is by introducing transition metal and rare earth oxides, such as copper [5-8], lanthanum [9-10], and iron oxides [11]. In particular, it has been shown that cobalt species has the potential of enhancing the photocatalytic activity of TiO_2 for various reactions [19-21]. The deposition of cobalt species on TiO_2 increased the degradation rate of acid red G due to the increase of the separation in the photogenerated electron-hole pairs [19]. Cobalt doped TiO_2 was reported to be a stable and efficient photocatalyst for hydrogen production from glycerol since the addition of cobalt was able to lower the electron-hole recombination with satisfactory light harvesting [20]. High photocatalytic activity of cobalt ion doped TiO_2 was also reported to against fungi, owing to ability to produce active oxidant species [21]. In these samples, cobalt existed as Co^{2+} [19-21] due to the low loading amount of cobalt precursor (2% or less). In contrast to these reports, cobalt doped TiO_2 showed no

photocatalytic activity for degradation of diquat dibromide monohydrate when the loading amount was high (5%) [22]. It was confirmed that cobalt was present as a mixed Co^{3+} and Co^{4+} that created oxygen vacancies that might act as electron traps that decreased the electrons in the conduction band, thus reducing the activity. The detrimental photocatalytic activity for degradation of Basic Blue 41 was also observed on cobalt modified- TiO_2 photocatalyst when mixed oxide of cobalt titanate (CoTiO_3) phase was formed [23]. In the present study, a simple impregnation method was used to prepare cobalt oxide-modified commercial Evonik P25 TiO_2 photocatalysts. The effect of cobalt oxide loading on the photocatalytic activity of TiO_2 was investigated for degradation of 2,4-D as the model pollutant.

EXPERIMENTAL SECTION

Materials

P25 TiO_2 (Evonik), cobalt(II) nitrate hexahydrate ($\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, Aldrich, $\geq 98\%$), and 2,4-D ($\text{C}_8\text{H}_6\text{Cl}_2\text{O}_3$, Sigma, $\geq 98\%$) were used without further purification.

Instrumentation

The instruments used for characterizations were X-ray diffractometer (XRD), scanning electron microscopy attached with energy dispersive X-ray (SEM-EDX), reflectance UV-visible and fluorescence spectrophotometers. UV spectrophotometer was also used to monitor the photocatalytic reaction.

Procedure

Preparation of photocatalysts

Certain amount of cobalt(II) nitrate hexahydrate was dissolved in 20 mL of double distilled water, followed by addition of P25 TiO_2 (1 g) in the solution. In order to obtain good dispersion, the mixture was ultrasonicated for 10 min at room temperature. The mixture was then stirred and heated at 80 °C until all solvent was removed. The dried powder was ground to a fine powder and calcined in air at 500 °C for 4 h. After calcination, resulted powder was ground and stored under ambient conditions. The prepared samples were labeled as x mol% $\text{CoO}/\text{P25 TiO}_2$, with x showed the ratio of Co to Ti (mol%) that varied in the range of 0.1–5 mol%. For comparison, the P25 TiO_2 was also treated in the same manner to the samples, except for the addition of the cobalt(II) nitrate hexahydrate.

Characterizations of photocatalysts

The crystal structure of prepared samples was investigated by an XRD using a Bruker Advance D8 diffractometer with Cu K α radiation ($\lambda = 1.5406 \text{ \AA}$, at 40 kV and 40 mA). SEM images, mapping, and EDX spectra were measured on a Hitachi Tabletop SEM TM 3000 attached with a Bruker EDX at the voltage of 15 kV. The samples were put on a carbon tape and measured without any coatings. The optical properties of the samples were analyzed by an Avantes spectrophotometer AvaSpec-ULS2048 using a reflection probe holder with angle of 45° and PTFE-coated white material as the reference sample. The emission spectra were measured at room temperature on a fluorescence spectroscopy using a JASCO FP-8500. The samples were put in the solid sample holder and the spectra were monitored at excitation wavelength of 218 nm.

Photocatalytic degradation of 2,4-D

The prepared samples were evaluated for degradation of 2,4-D at room temperature under UV light irradiation. Prior to irradiation, the sample (50 mg) was dispersed in 2,4-D solution (50 mL, 0.5 mM) and stirred in the dark condition for 1 h to achieve the adsorption-desorption equilibrium. The reaction was carried out for 1 h under irradiation by a 200 W Xe-Hg lamp, which light intensity was 15 mW cm⁻² and it was equipped with an IR cut off filter. The remaining amount of 2,4-D after each reaction was determined by UV spectrophotometer using a Thermo Scientific Genesys 10S. The monitored wavelength was 283 nm. The percentage of 2,4-D degradation was then calculated from the ratio of concentrations between the reacted and the initial concentrations of 2,4-D.

RESULT AND DISCUSSION

Properties of Photocatalysts

Fig. 1 shows XRD patterns of bare P25 TiO₂ and cobalt oxide-modified P25 TiO₂ samples. It was obvious that P25 TiO₂ has both anatase and rutile phases (Fig. 1 (a)). The diffraction peaks of P25 TiO₂ were not much influenced by the addition of cobalt oxide (Fig. 1(b)-(e)). Moreover, no other new diffraction peak was observed after the modification, which was in good agreement with reported literature on cobalt-doped TiO₂ samples with low loading of cobalt precursor [20]. These results suggested that the amount of added cobalt oxide might be too low to be detected by the present XRD or the cobalt oxide might be dispersed well on the surface of TiO₂. Even though the diffraction peaks of cobalt oxide could not be detected by XRD, it has been reported that cobalt oxide would exist as cobalt monoxide (CoO) on supported samples when the loading amount of added

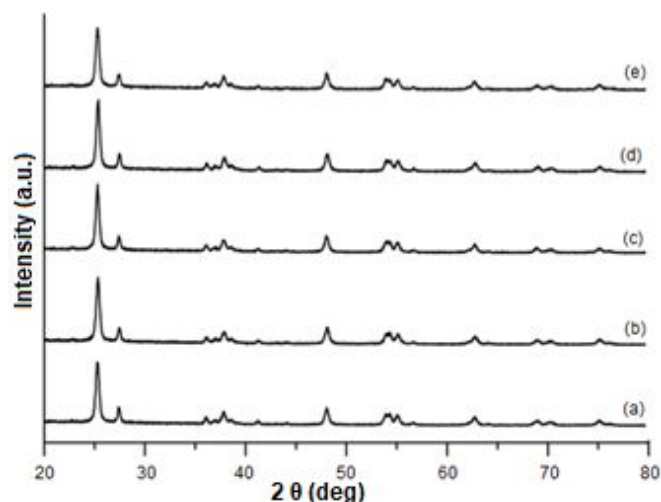


Fig 1. XRD patterns of (a) P25 TiO₂, (b) 0.1 mol% CoO/P25 TiO₂, (c) 0.5 mol% CoO/P25 TiO₂, (d) 1 mol% CoO/P25 TiO₂, and (e) 5 mol% CoO/P25 TiO₂ samples

Table 1. Crystallite size and anatase-rutile ratio of P25 TiO₂ and cobalt oxide-modified P25 TiO₂ samples

Samples	Crystallite size (nm)	Anatase-rutile ratio (%)
Bare P25 TiO ₂	17.0	72:28
0.1 mol% CoO/P25 TiO ₂	17.1	75:25
0.5 mol% CoO/P25 TiO ₂	17.5	75:25
1 mol% CoO/P25 TiO ₂	16.6	75:25
5 mol% CoO/P25 TiO ₂	15.3	74:26

cobalt precursor was low [20,24]. Therefore, the most possible cobalt species formed on the present samples would be CoO.

Table 1 lists the crystallite size and the ratio of anatase to rutile for the P25 TiO₂ and cobalt oxide-modified P25 TiO₂ samples. The crystallite size was determined by Scherrer equation using the most intense peak around 2 θ of 25.3°, while the anatase to rutile ratio was calculated based on the intensity of the most intense peaks at around 2 θ of 25.3 and 27.4° for anatase and rutile, respectively. It was obtained that all samples have similar crystallite size to each other, which was in the range of 15–17 nm, and also similar anatase to rutile ratio, which anatase composition was in the range of 72–75%. These results confirmed that the addition of CoO did not affect the structural properties of P25 TiO₂.

In order to confirm the presence of CoO on the modified P25 TiO₂ samples, the samples were analyzed by the SEM-EDX. As representatives, mapping images of the modified P25 TiO₂ with the lowest and largest loading amounts of CoO, which are 0.1 and 5 mol%, respectively, are shown in Fig. 2(a) and (b). It was obvious that carbon, oxygen, titanium, and cobalt were detected on these samples. Carbon

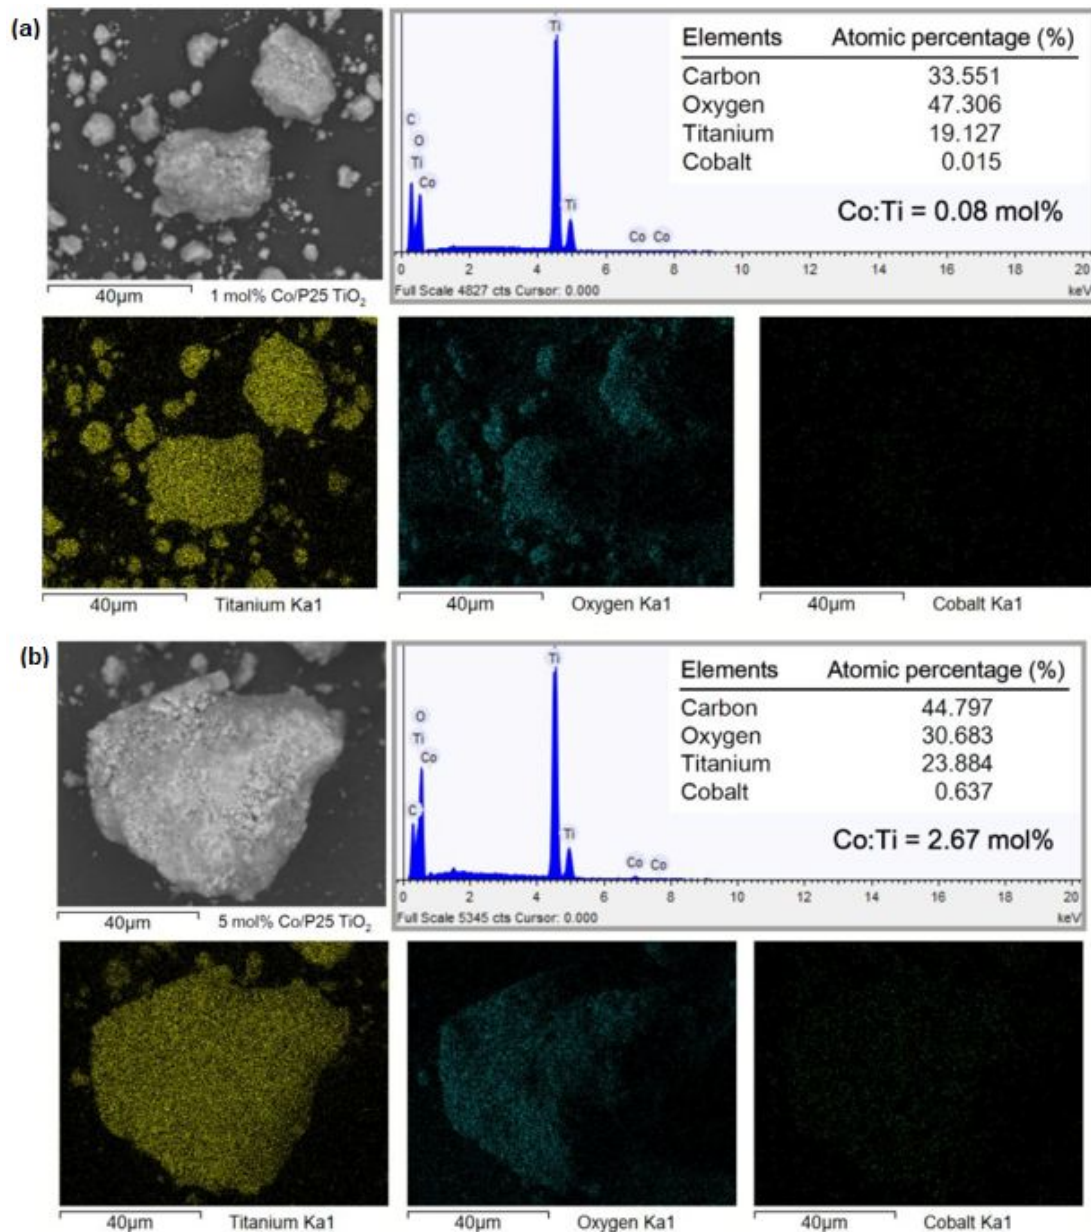


Fig 2. SEM images with element mappings and EDX spectra of (a) 0.1 mol% CoO/P25 TiO₂ and (b) 5 mol% CoO/P25 TiO₂ samples

parts of the samples. It is worth noted that the presence was observed as the carbon tape was used for the measurements. On the other hand, as expected the titanium and oxygen were distributed uniformly in all of cobalt was clarified even at the 0.1 mol% Co/P25 TiO₂ (Fig. 2(a)). The cobalt was found to be dispersed on the P25 TiO₂ for both samples. Other samples, which are the 0.5 mol% Co/P25 TiO₂ and the 1 mol% Co/P25 TiO₂ also showed similar mapping images to these samples (not shown).

Fig. 2 also shows the composition of the elements based on the quantification of the EDX spectra. The ratio

of cobalt to titanium was determined to be 0.08 mol% for the 0.1 mol% CoO/P25 TiO₂ and 2.67 mol% for the 5 mol% CoO /P25 TiO₂. Therefore, it can be proposed that the detected amount of cobalt was very close to the theoretical added amount for samples with the low loading of CoO. As for high loading sample, the detected cobalt amount was relatively less than the added one. This might be due to the loss of the cobalt precursor during the preparation process since not all of CoO can be impregnated successfully on the P25 TiO₂ when the amount was too high. As for other samples, the ratio of cobalt to titanium was determined

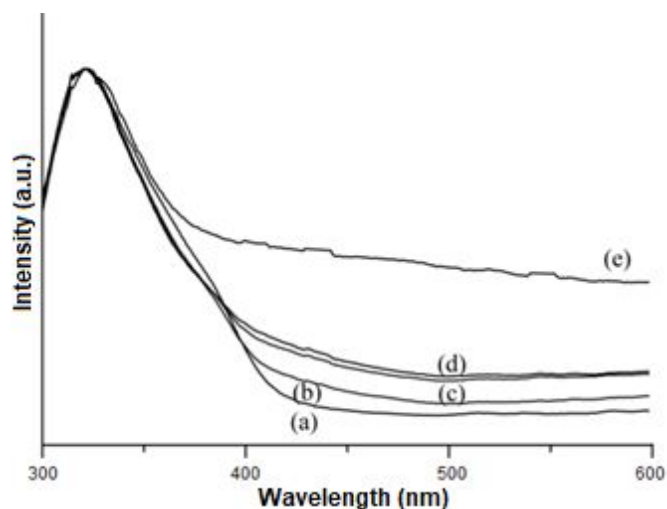


Fig 3. Normalized UV-visible spectra of (a) P25 TiO₂, (b) 0.1 mol% CoO/P25 TiO₂, (c) 0.5 mol% CoO/P25 TiO₂, (d) 1 mol% CoO/P25 TiO₂, and (e) 5 mol% CoO/P25 TiO₂ samples

to be 0.30 and 1.14 mol% for the 0.5 mol% CoO/P25 TiO₂ and the 1 mol% CoO/P25 TiO₂, respectively.

The absorption spectra of P25 TiO₂ and the prepared cobalt oxide-modified P25 TiO₂ samples are shown in Fig. 3. Since the P25 TiO₂ has white color, the P25 TiO₂ did not show any absorption in the visible region (Fig. 3(a)). On the other hand, cobalt oxide-modified P25 TiO₂ samples have olive-green color that indicated the presence of CoO, in which the color became darker with the increase amount of CoO loading. In good agreement with the color appearance, these modified samples gave the additional absorption band above 400 nm (Fig. 3(b)-(e)). The background level absorption above 400 nm could be more observed with more addition of CoO, clearly suggesting that the CoO was the source of such visible light absorption. Even though the addition of CoO was found to shift the absorption of TiO₂ to longer wavelength, the absorption edge of P25 TiO₂ was not much influenced. This result suggested that CoO did not much alter the band gap of P25 TiO₂. This was reasonable since the cobalt precursor was impregnated on the surface of P25 TiO₂ as CoO. Therefore, it was different from the case when the cobalt ion was doped into the TiO₂ after reduction process, where the cobalt caused prominent shift of band edge from UV to visible region (from 3.2 to 2.7 eV) [20].

Fig. 4 shows the emission spectra of P25 TiO₂ and the prepared cobalt oxide-modified P25 TiO₂ samples when they were monitored at the excitation wavelength of 218 nm. As shown in Fig. 4(a), it was confirmed that the P25 TiO₂ showed strong emission spectrum with emission peaks at 410, 465, and 544 nm. It has been reported that the peak around 410 nm would correspond

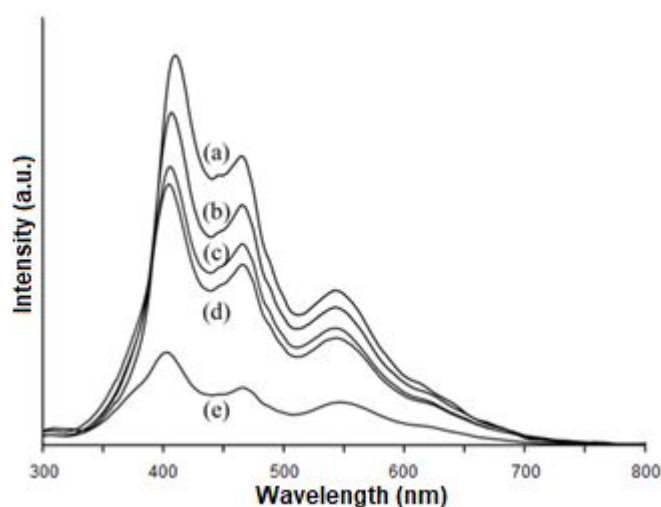


Fig 4. Emission spectra of (a) P25 TiO₂, (b) 0.1 mol% CoO/P25 TiO₂, (c) 0.5 mol% CoO/P25 TiO₂, (d) 1 mol% CoO/P25 TiO₂ and (e) 5 mol% CoO/P25 TiO₂ samples

to the radiative recombination of self-trapped exciton and the other two emission peaks at 465 and 544 nm would be due to the charge transfer of an oxygen vacancy trapped electron [11]. Addition of CoO did not give the formation of any new emission peaks, but decreased the emission intensity of the bare P25 TiO₂ (Fig. 4(b)-(e)). The emission intensity was decreased with the increase of the CoO loading. It has been generally understood that the emission spectrum is attributed to the radiative recombination of the excited electron and holes [25-26]. Therefore, the decrease in the emission intensity could indicate the role of cobalt species to lower the electron-holes recombination as has been proposed previously [19-20]. Even though the suppression of electron-hole recombination can be helpful to improve the efficiency of P25 TiO₂, there would be a balance between the suppression of the recombination and availability of electrons in the conduction band for the reaction.

Photocatalytic Activity and Proposed Mechanism

After 1 h under dark condition, all samples gave similar adsorption of 2,4-D in the range of 10.6-13.2%, suggesting that the present addition of cobalt oxide did not much vary the amount of surface sites interacting with 2,4-D molecules. In order to investigate the effect of the CoO loading on the photocatalytic activity of P25 TiO₂, the samples were evaluated for degradation of 2,4-D under UV light irradiation for 1 h. Fig. 5 shows the dependence of photocatalytic activity on the amount of CoO loading after excluding the adsorption part. It can be clearly shown that the photocatalytic activity of P25 TiO₂ increased from 49.6 to 54.6% with

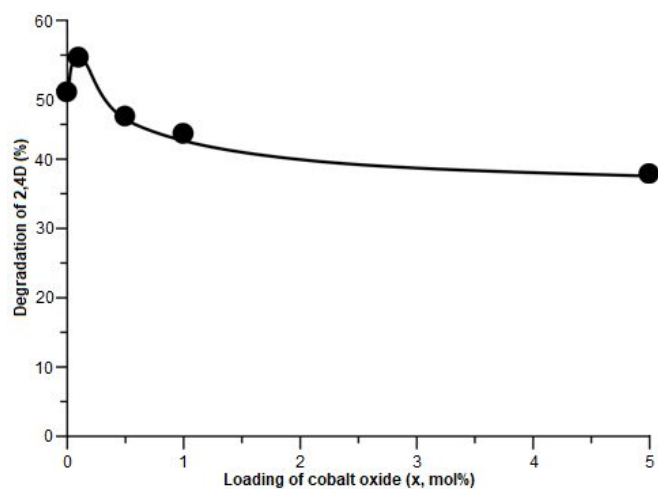


Fig 5. Photocatalytic degradation of 2,4-D on the P25 TiO₂ and cobalt oxide-modified P25 TiO₂ photocatalysts

addition of 0.1 mol% CoO. Unfortunately, higher loading of CoO caused lower photocatalytic activity. When the loading amount was 5 mol%, the activity dropped to only 37.8%. This result clearly suggested that the small amount of CoO, which was 0.1 mol%, was the optimum amount to give the optimum activity for this cobalt oxide-modified P25 TiO₂ series. The higher photocatalytic activity would be originated from the lower electron-hole recombination, which enhanced the possibility for the degradation of 2,4-D pollutant. On the other hand, the addition of higher loading might result in the less available electrons in the conduction band of P25 TiO₂, and thus reducing the efficiency of the P25 TiO₂.

Based on the characterization and photocatalytic activity results, the pathways of charge transfers can be proposed below. When the CoO/P25 TiO₂ was irradiated under UV light irradiation, electrons in the valence band of P25 TiO₂ would be excited to the conduction band resulting in the formation of holes in the valence band. The excited electrons would react with adsorbed oxygen to produce superoxide radicals, while holes would oxidize 2,4-D. Holes could also oxidize water to produce hydroxyl radicals. However, the contribution of hydroxyl radicals to degrade 2,4-D would not be as high as those of superoxide radicals and holes due to the low formation of hydroxyl radicals [11]. In addition to this pathway, electrons could be also trapped by cobalt species, which in turn caused a better separation of electrons and holes, and thus, higher photocatalytic activity.

CONCLUSION

The cobalt oxide-modified P25 TiO₂ photocatalysts were successfully prepared by the impregnation method, followed by the calcination process. The addition of CoO

did not affect much on the structural properties of P25 TiO₂. Its presence was confirmed by SEM-EDX in which the added CoO was dispersed well on the P25 TiO₂. The CoO gave additional absorption at visible light region but did not alter the band gap of the P25 TiO₂. Small amount of CoO was found to decrease the fluorescence emission intensity that represented the reduced electron-hole recombination process. It was obtained that the CoO with 0.1 mol% gave the optimum photocatalytic activity.

ACKNOWLEDGEMENT

The research leading to these results has received funding from the European Union Seventh Framework Program (EU-FP7) under 4G-PHOTOCAT grant (agreement no.: 309636). This work has been also financially supported by the Ministry of Higher Education (MOHE) and Universiti Teknologi Malaysia (UTM, Malaysia) through the international contract matching grant (cost center code: R.J130000.7626.4C035). Aseptec Sdn. Bhd. and Hi-Tech Instruments Sdn. Bhd. were greatly acknowledged for providing the AvaSpec-ULS2048 and the Hitachi TM3000, respectively for the sample analyses.

REFERENCES

- [1] Burns, C.J., and Swaen, G.M.H., 2012, Review of 2,4-dichlorophenoxyacetic acid (2,4-D) biomonitoring and epidemiology, *Crit. Rev. Toxicol.*, 42 (9), 768–786.
- [2] Vega, A.A., Imoberdorf, G.E., and Mohseni, M., 2011, Photocatalytic degradation of 2,4-dichlorophenoxyacetic acid in a fluidized bed photoreactor with composite template-free TiO₂ photocatalyst, *Appl. Catal., A*, 405 (1-2), 120–128.
- [3] Liu, X., Tang, Y., Luo, S., Wang, Y., Zhang, X., Chen, Y., and Liu, C., 2013, Reduced graphene oxide and CuInS₂ co-decorated TiO₂ nanotube arrays for efficient removal of herbicide 2,4-dichlorophenoxyacetic acid from water, *J. Photochem. Photobiol., A*, 262, 22–27.
- [4] Tang, Y., Luo, S., Teng, Y., Liu, C., Xu, X., Zhang, X., and Chen, L., 2012, Efficient removal of herbicide 2,4-dichlorophenoxyacetic acid from water using Ag/reduced graphene oxide co-decorated TiO₂ nanotube arrays, *J. Hazard. Mater.*, 241-242, 323–330.
- [5] Roslan, N.A., Lintang, H.O., and Yuliati, L., 2015, Enhanced photocatalytic performance of copper-modified titanium dioxide prepared by UV reduction method, *Adv. Mater. Res.*, 1112, 180–183.

- [6] Siah, W.R., Lintang, H.O., Shamsuddin, M., Yoshida, H., and Yuliati, L., 2016, Masking effect of copper oxide photodeposited on titanium dioxide: exploring UV, visible, and solar light activity, *Catal. Sci. Technol.*, 6 (13), 5079–5087.
- [7] Yuliati, L., Siah, W.R., Roslan, N.A., Shamsuddin, M., and Lintang, H.O., 2016, Modification of titanium dioxide nanoparticles with copper oxide co-catalyst for photocatalytic degradation of 2,4-dichlorophenoxyacetic acid, *MJAS*, 20 (1), 171–178.
- [8] Lee, S.C., Hasan, N., Lintang, H.O., Shamsuddin, M., and Yuliati, L., 2016, Photocatalytic removal of 2,4-dichlorophenoxyacetic acid herbicide on copper oxide/titanium dioxide prepared by co-precipitation method, *IOP Conf. Ser. Mater. Sci. Eng.*, 107, 012012.
- [9] Siah, W.R., Roslan, N.A., Lintang, H.O., Shamsuddin, M., and Yuliati, L., 2015, Photocatalytic removal of 2,4-D herbicide on lanthanum oxide-modified titanium dioxide, *Adv. Mater. Res.*, 1112, 168–171.
- [10] Siah, W.R., Lintang, H.O., and Yuliati, L., 2017, Role of lanthanum species in improving the photocatalytic activity of titanium dioxide, *Catal. Sci. Technol.*, 7, 159–167.
- [11] Lee, S.C., Lintang, H.O., and Yuliati, L., 2017, High photocatalytic activity of Fe₂O₃/TiO₂ nanocomposites prepared by photodeposition for degradation of 2,4-dichlorophenoxyacetic acid, *Beilstein J. Nanotechnol.*, 8, 915–926.
- [12] Lee, H., Park, S.H., Park Y.K., Kim, S.J., Seo, S.G., Ki, S.J., and Jung, S.C., 2015, Photocatalytic reactions of 2,4-dichlorophenoxyacetic acid using a microwave-assisted photocatalysis system, *Chem. Eng. J.*, 278, 259–264.
- [13] Nejati, K., Davary, S., and Saati, M., 2013, Study of 2,4-dichlorophenoxyacetic acid (2,4-D) removal by Cu-Fe-layered double hydroxide from aqueous solution, *Appl. Surf. Sci.*, 280, 67–73.
- [14] Pei, C.C., and Chu, W., 2013, The photocatalytic degradation and modeling of 2,4-dichlorophenoxyacetic acid by bismuth tungstate/peroxide, *Chem. Eng. J.*, 223, 665–669.
- [15] Malato, S., Fernández-Ibáñez, P., Maldonado, M.I., Blanco, J., and Gernjak, W., 2009, Decontamination and disinfection of water by solar photocatalysis: Recent overview and trends, *Catal. Today*, 147 (1), 1–59.
- [16] Chong, M.N., Jin, B., Chow, C.W.K., and Saint, C., 2010, Recent developments in photocatalytic water treatment technology: A review, *Water Res.*, 44 (10), 2997–3027.
- [17] Teh, C.M., and Mohamed, A.R., 2011, Roles of titanium dioxide and ion-doped titanium dioxide on photocatalytic degradation of organic pollutants (phenolic compounds and dyes) in aqueous solutions: A review, *J. Alloys Compd.*, 509 (5), 1648–1660.
- [18] Fajriati, I., Mudasir, and Wahyuni, E.T., 2014, Photocatalytic decolorization study of methyl orange by TiO₂-chitosan nanocomposites, *Indones. J. Chem.*, 14 (3), 209–218.
- [19] Gracien, E.B., Shen, J., Sun, X., Liu, D., Li, M., Yao, S., and Su, J., 2007, Photocatalytic activity of manganese, chromium and cobalt-doped anatase titanium dioxide nanoporous electrodes produced by re-anodization method, *Thin Solid Films*, 515 (13), 5287–5297.
- [20] Sadanandam, G., Lalitha, K., Kumari, V.D., Shankar, M.V., and Subrahmanyam, M., 2013, Cobalt doped TiO₂: A stable and efficient photocatalyst for continuous hydrogen production from glycerol: Water mixtures under solar light irradiation, *Int. J. Hydrogen Energy*, 38 (23), 9655–9664.
- [21] Tatlıdil, I., Bacaksız, E., Buruk, C.K., Breen, C., and Sökmen, M., 2012, A short literature survey on iron and cobalt ion doped TiO₂ thin films and photocatalytic activity of these films against fungi, *J. Alloys Compd.*, 517, 80–86.
- [22] Castro, A.L., Nunes, M.R., Carvalho, M.D., Ferreira, L.P., Jumas, J.C., Costa, F.M., and Florêncio, M.H., 2009, Doped titanium dioxide nanocrystalline powders with high photocatalytic activity, *J. Solid State Chem.*, 182 (7), 1838–1845.
- [23] Bouras, P., Stathatos, E., and Lianos, P., 2007, Pure versus metal-ion-doped nanocrystalline titania for photocatalysis, *Appl. Catal., B*, 73 (1-2), 51–59.
- [24] Liu, J., Zhao, Z., Wang, J., Xu, C., Duan, A., Jang, G., and Yang, Q., 2008, The highly active catalysts of nanometric CeO₂-supported cobalt oxides for soot combustion, *Appl. Catal., B*, 84 (1-2), 185–195.
- [25] Li, D., Haneda, H., Hishita, S., and Ohashi, N., 2005, Visible-light-driven N-F-codoped TiO₂ photocatalysts. 2. Optical characterization, photocatalysis, and potential application to air purification, *Chem. Mater.*, 17 (10), 2596–2602.
- [26] Zhang, J., Hu, Y., Matsuoka, M., Yamashita, H., Minagawa, M., Hidaka, H., and Anpo, M., 2001, Relationship between the local structures of titanium oxide photocatalysts and their reactivities in the decomposition of NO, *J. Phys. Chem. B*, 105 (35), 8395–8398.