

IJC2020

by Leny Yuliaty

Submission date: 27-Jul-2022 03:51PM (UTC+0800)

Submission ID: 1875756275

File name: with_Enhanced_Photocatalytic_Activity_for_Phenol_Degradation.pdf (723.24K)

Word count: 6911

Character count: 35726

Optimized Synthesis Temperature and Time to Obtain Crystalline Carbon Nitride with Enhanced Photocatalytic Activity for Phenol Degradation

Leny Yuliati^{1,2,3,*}, Mohd Hayrie Mohd Hatta^{4,5}, Siew Ling Lee^{3,4}, and Hendrik Oktendy Lintang^{1,2,3}

¹Ma Chung Research Center for Photosynthetic Pigments, Universitas Ma Chung, Villa Puncak Tidar N-01, Malang 65151, East Java, Indonesia

²Department of Chemistry, Faculty of Science and Technology, Universitas Ma Chung, Villa Puncak Tidar N-01, Malang 65151, East Java, Indonesia

³Center for Sustainable Nanomaterials, Ibnu Sina Institute for Scientific and Industrial Research, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia

⁴Department of Chemistry, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia

⁵Foundation in Science, Faculty of Medicine, ASIA Metropolitan University, 81750, Johor Bahru, Johor, Malaysia

* Corresponding author:

email: leny.yuliati@machung.ac.id

Received: December 17, 2019

Accepted: March 26, 2020

DOI: 10.22146/ijc.52345

Abstract: In this work, the crystalline carbon nitride photocatalysts were synthesized by an ionothermal technique with varied synthesis temperature of 500, 550, and 600 °C, and varied synthesis time of 2, 4, and 6 h. Fourier transform infrared spectra showed the successful formation of the prepared carbon nitrides from their characteristic vibration peaks. X-ray diffraction patterns suggested that the same phase of poly(triazine imide) and heptazine could be observed, but with different crystallinity. The optical properties showed that different temperatures and synthesis time resulted in the different band gap energy (2.72–3.02 eV) as well as the specific surface area (24–73 m² g⁻¹). The transmission electron microscopy image revealed that the crystalline carbon nitride has a near-hexagonal prismatic crystallite size of about 50 nm. Analysis by high-performance liquid chromatography showed that the best photocatalytic activity for phenol degradation under solar light simulator was obtained on the crystalline carbon nitride prepared at 550 °C for 4 h, which would be due to the high crystallinity, suitable low band gap energy (2.82 eV), and large specific surface area (73 m² g⁻¹). Controlling both the temperature and synthesis time is shown to be important to obtain the best physicochemical properties leading to high activity.

Keywords: carbon nitride; crystallinity; phenol degradation; synthesis temperature; synthesis time

■ INTRODUCTION

Phenol is one of the major organic pollutants that exist in the industry effluents [1]. Even though at low concentration, phenol has high toxicity. An alternative method that offers green and clean technology to treat phenol is the photocatalytic degradation process. Many studies have been focused on the development of titanium dioxide (TiO₂)-based photocatalysts for various photocatalytic degradation reactions [2-4], which are mostly due to the high activity of TiO₂ under ultraviolet

(UV) irradiation. However, owing to the large portion of visible light in the sunray, the development of visible light active photocatalysts has been an important task in the photocatalysis field. Since TiO₂ does not absorb visible light, some modifications are required, such as by doping or making a composite with another visible light-active semiconductor [5-7]. In addition to these efforts, studies on the potential materials that are visible light active are still highly required. One of the fascinating choices for the visible light active photocatalysts is

carbon nitride (CN). Even though CN has been investigated for years, many reported literatures showed that the synthesized CN was in the amorphous form [8-14]. While the CN showed photocatalytic activity under visible light, the CN with the amorphous phase has been reported to show lower photocatalytic performance in the catalytic process as compared to the crystalline one. A drastic enhancement in the photocatalytic activity of the CN has been reported to occur over the crystalline CN either for photocatalytic degradation of organic compounds or for hydrogen production [15-19].

In photocatalysis, the directional flow of electrons depends on the organization of the molecules in the structure concerning their crystalline [20-22]. Moreover, the crystalline structure would demonstrate faster electron movement as the direction is confined. The fast rate of electron diffusion would reduce the trapping and de-trapping effect; thus, the rate of electron-hole recombination would be decreased [23]. In the case of crystalline CN, the enhanced photocatalytic activity could also be additionally caused by the improved light absorption due to the extended π -conjugated system and the increased rigidity of the polymer backbones [24]. Since the photocatalytic properties are sensibly affected by the crystallinity of the photocatalyst, constructing a crystalline photocatalyst that is active under natural sunlight is a promising work and highly recommended but can be a challenging task to be achieved.

Several methods to produce the crystalline CN have been examined. Recently, it was reported that the crystalline CN could be synthesized via an ionic melt polycondensation of urea precursor in the presence of potassium chloride-lithium chloride (KCl-LiCl) salt melt [15]. Bhunia et al. produced the crystalline carbon nitride by combining the supramolecular aggregation and polycondensation of an ionic melt using melamine, 2,4,6-triaminopyrimidine, and LiCl/KCl mixture [16]. These two methods produced crystalline CN having not only the structure of graphitic CN but also the poly(triazine imide)-like structure [15-16]. The better-ordered structure of the graphitic CN was observed by using a thermal condensation of melem but must be put under a pure oxygen atmosphere [17]. Another method was also

reported involving an additional acidic washing process using hydrogen chloride (HCl) after the polycondensation of melamine in the presence of KCl and LiCl [18]. Another synthesis method, a rapid polymerization of melamine without the early heating process, was proposed to produce the crystalline CN [19]. However, these last-mentioned three methods only produced CN having the structure of graphitic CN with a better order in the interlayer stacking and in-plane repeated units. These semi-crystalline CN materials are usually obtained when the precursor is thermally polymerized [24].

Since we aim to get the crystalline CN, the synthesis method that has been proven to give the structure of crystalline CN shall be employed. Among the techniques mentioned above, the one using ionothermal technique with the help of KCl-LiCl salt melt has been shown to require fewer chemicals to obtain the crystalline CN having the poly(triazine imide)-like structure [15]. Moreover, the resulted crystalline CN was confirmed to give higher photocatalytic activity for phenol degradation under visible light than the amorphous CN. However, a detailed study of the optimized synthesis temperature and time for this method has not been addressed yet. In order to optimize the photocatalytic efficiency of the crystalline CN, in this work, the effects of synthesis temperature and time on the properties and photocatalytic activity of the crystalline CN were investigated. This work demonstrated that the optimized synthesis temperature and time were important parameters to obtain the optimized photocatalytic activity of the crystalline CN. As high as 3.4 times higher photocatalytic activity was observed on the sample synthesized under the optimized conditions than those prepared under the non-optimized one.

■ EXPERIMENTAL SECTION

Materials

For the preparation of CN materials, urea ($\text{CH}_4\text{N}_2\text{O}$, QR C , 99%) was used as carbon and nitrogen-rich precursors. Ethanol ($\text{C}_2\text{H}_5\text{OH}$, HmBG Chemicals, 99.98%) was used as a solvent in the

preparation of CN. For the preparation of crystalline CN, the ionic solvents used were lithium chloride (LiCl, Sigma-Aldrich, 99%) and potassium chloride (KCl, Fisher Chemicals, 99.5%). The model of organic pollutant used for this study was phenol (C₆H₆O, Scharlau Chemie, 99.5%).

Procedure

Synthesis of crystalline carbon nitride

The crystalline carbon nitride was prepared in a similar way to the reported literature [15]. In order to investigate the effect of synthesis temperature (500, 550, and 600 °C), other synthesis parameters including the amount of precursor (2 g), synthesis time (4 h), and amount of salts melt (2.74 g KCl, 2.26 g LiCl) were fixed. The final products were labeled as CN-*T*, which were CN-500, CN-550, and CN-600. The synthesis time was varied to 2, 4, and 6 h to obtain the optimum time. In this part, the amount of precursor (2 g), reaction temperature (550 °C), and amount of salts melt (2.74 g KCl and 2.26 g LiCl) were fixed. The final samples were labeled as CN-*t* in which *t* refers to 2, 4, and 6 h.

Characterizations of crystalline carbon nitride

The prepared CN materials were characterized using several instruments. The structural properties were identified using a powder X-ray diffractometer (XRD). The XRD patterns were recorded using Bruker D8 Advance with CuK_α irradiation ($\lambda = 1.5406 \text{ \AA}$). The optical properties were determined by a diffuse reflectance ultraviolet-visible (DR UV-vis) spectroscopy using a Shimadzu UV-2600 DR UV-vis spectrophotometer with wavelength recorded in the range of 220 to 800 nm. The chemical bonds and functional groups were determined by using a Fourier transform infrared spectroscopy (FTIR, Nicolet-iS50). The technique used in the characterization was the KBr pellet technique. The nitrogen (N₂) adsorption-desorption isotherm analysis at -196.15 °C (77K) using a Quantachrome NOVAtouch LX4 instrument was deployed in order to investigate the specific surface area (SA). All the samples were dried at 100 °C in the oven before the measurement. For the degassing part, the samples were heated at 180 °C for 3 h at the ramp of 10 °C/min. The best CN material was also

characterized by a transmission electron microscope (TEM, JEOL JEM-2100).

Photocatalytic degradation of phenol

The photocatalyst (0.05 g) was dispersed in 100 mL of a beaker containing 50 mL of 50 ppm phenol. Prior to the photocatalytic reaction, the solution was stirred continuously in the dark condition for 30 min to reach the equilibrium of adsorption-desorption. The photocatalytic reaction was carried out under solar light simulator irradiation (150 W, $\lambda > 230 \text{ nm}$, and $I = 110,000 \text{ Lux}$) for 6 h. The final remaining concentration of the solution was determined by using high-performance liquid chromatography (HPLC, Shimadzu, LC-20AT) equipped with a UV detector. The final concentration of phenol was determined using the ratio of degraded phenol to its initial concentration.

RESULTS AND DISCUSSION

Effect of Synthesis Temperature

The XRD patterns of the prepared CN-*T* samples are presented in Fig. 1. Based on the spectra, all samples showed crystalline properties with at least one crystalline peak of (210) plane was observed. Two most intense and broad peaks at 2θ of ca. 27 and 12° corresponded to an interlayer distance of graphite-like CN and distance of the in-plane arrangement of nitrogen-linked heptazine or poly(triazine imide) units, respectively [8-19,24-31]. Both peaks were observed in all samples. The CN-500 showed at least one crystalline peak, which was observed at 2θ of ca. 31.9° (210), indicating the crystallization could be initiated at a temperature of 500 °C.

When the synthesis temperature was increased to 550 °C, more crystalline peaks were visualized, mainly at 2θ of 20.7 (110), 24.5 (200), 29.3 (102) and 32.4° (210), owing to the poly(triazine imide) units [15-16,25-26]. Similar crystalline peaks were also observed when the synthesis temperature was increased to 600 °C, but the resulted CN-600 was composed of the hybrid of heptazine-based and poly(triazine imide) units. The amorphous phase (heptazine-based units) was likely to be induced at a higher temperature as can be seen at 2θ of 27.8°.

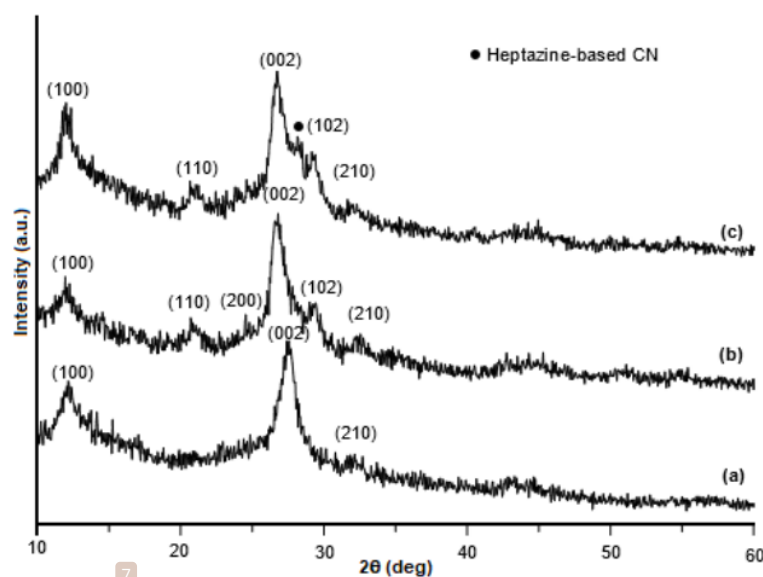


Fig 1. XRD patterns of (a) CN-500, (b) CN-550, and (c) CN-600

It was demonstrated that increasing the synthesis temperature from 500 to 550 °C resulted in the changes in phase structure from heptazine-based units (amorphous CN) to poly(triazine imide) (crystalline CN) with high crystalline phase, owing to its high thermal stability compared to amorphous CN at high temperature in the presence of molten salts. Similar results on the changes of the crystallinity phase were also reported on crystalline CN prepared by urea-based precursor when temperature variation was carried out [27]. The presence of the amorphous phase at a high temperature (600 °C) might be related to the binary phase properties of KCl-LiCl. In ionothermal synthesis, the molten salts were required as the ionic solvent for the growth of crystallization. As the temperature increased, the KCl-LiCl would consist of a mixture of both solid salts and molten salts. Since more solid salts in the eutectic mixture are formed at high temperature, it is believed that the crystallization could not occur, and thus leading to the formation of heptazine-based units. All these XRD results demonstrated that the crystallinity phase could be tuned via controlling the temperature during the ionothermal synthesis.

The optical properties of the prepared CN-T photocatalysts were investigated by the DR UV-vis

spectrophotometer. Fig. 2 shows the absorption spectra of the CN-500, the CN-550, and the CN-600. Three major peaks were observed in all of the samples. The peak at low region (*ca.* 260 nm) was attributed to C-N indicating the $\pi \rightarrow \pi^*$ transition, while the peak at region *ca.* 320 nm corresponded to the C=O functional group indicating the $\pi \rightarrow \pi^*$ and $n \rightarrow \pi^*$ transitions. The presence of the C=O functional group indicated the less condensation of urea precursor during the polymerization process [28]. Meanwhile, the peak at 366 nm corresponded to the C-N functional group [1,29-31].

The decreased intensity of the C=N and C-N peaks on the CN-500 was due to the incomplete polymerization of CN. It was worthy to note that the CN-550 showed a decreased intensity of the C=O peak, suggesting that the temperature of 550 °C could eliminate the C=O groups and induced the crystallization, forming a highly condensed CN network. When the synthesis temperature was raised to 600 °C, the CN-600 showed the presence of the C=O peak, and the absorption edge was slightly increased to a longer wavelength. As shown in Fig. 2, the CN-600 showed absorption up to 450 nm, while sample CN-550 showed absorption up to 430 nm.

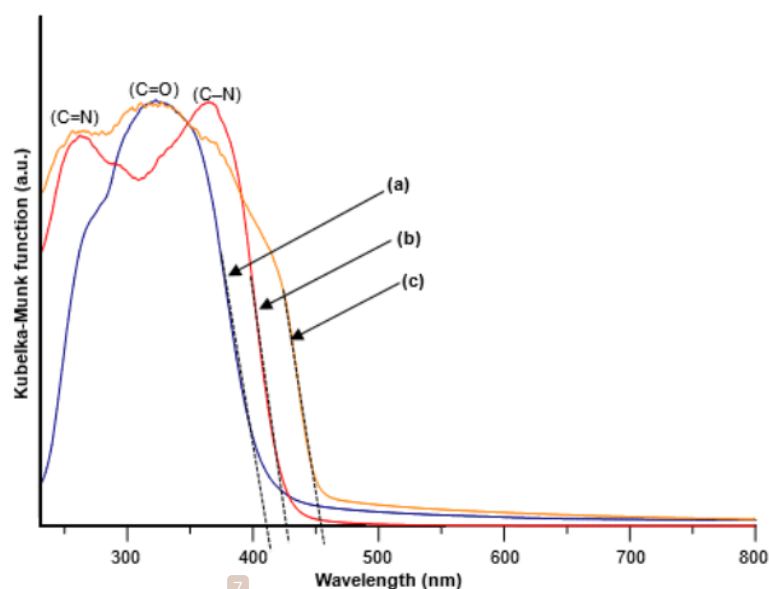


Fig 2. DR UV-vis spectra of (a) CN-500, (b) CN-550, and (c) CN-600

On the other hand, sample CN-500 showed a minimum absorption at region *ca.* 410 nm. This result demonstrated that increasing the synthesis temperature increased the visible light absorption. The altered optical properties might be related to the color changes of the prepared CN samples as the CN-500 showed a pale yellow, while the CN-550 and the CN-600 samples showed a yellowish and brownish yellow color, respectively.

It was revealed that the hybrid of heptazine and poly(triazine imide) CN enhanced the visible light absorption to longer wavelength, indicating a decrease in the band gap energy with increasing the synthesis temperature. Fig. 3 shows the band gap energy of CN-*T* samples estimated from the Tauc plot. The estimated band gap values for CN-500, CN-550, and CN-600 were 3.05, 2.82, and 2.72 eV, respectively. It has been reported that the band gap energy of the material is one of the important properties that can affect the photocatalytic performance [9-10]. Based on Fig. 3, it was shown that the synthesis temperature has a strong impact on the band gap energy values, which could be associated with the photocatalytic activity. As the synthesis temperature increased, the band gap energy of CN-*T* samples was

narrowed down, and the visible light absorption was enhanced. These results suggested that the band gap energy of CN can be tuned by controlling the synthesis temperature.

The characteristics of the chemical bonding and functional groups of the CN-*T* samples were studied by FTIR spectrometer. Fig. 4 shows the FTIR spectra of (CN-500, CN-550, and CN-600). From the spectra, it could be noted that increasing synthesis temperature did not result in significant changes in the functional groups. The peaks observed at the regions of 810 and 1200–700 cm^{-1} indicated the successful formation of CN heterocycles, thus, suggesting that the CN material could be synthesized at temperatures ranging from 500 to 600 °C. The peak at *ca.* 810 cm^{-1} corresponded to the bending mode of out-of-plane triazine units, while the multiple bands at *ca.* 1200–1700 cm^{-1} corresponded to the stretching mode of heptazine and/or poly(triazine imide) units [8,11,15,17-21,24-26,28].

On the other hand, the formation of both C=N and N=C=N at 2170 cm^{-1} was due to the broke of the CN continuity network [8,15,28], owing to the intercalation of lithium and chloride ions that resulted in the formation

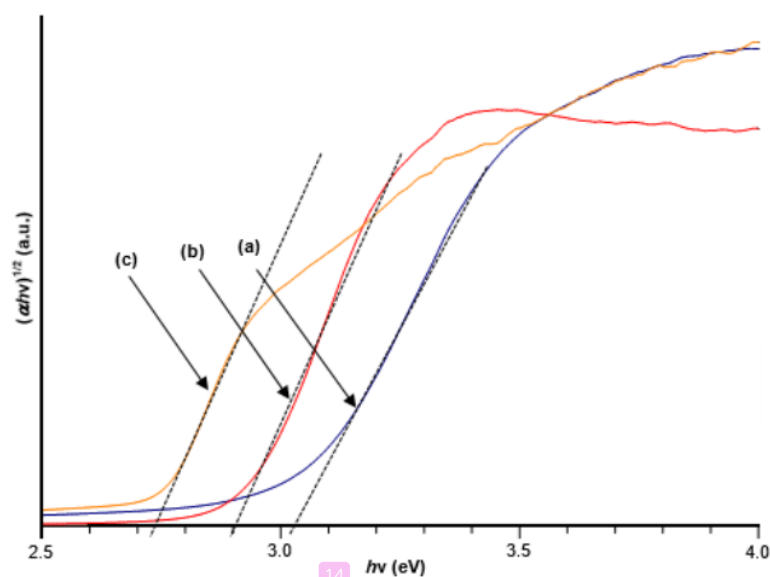


Fig 3. Tauc plots of (a) CN-500, (b) CN-550, and (c) CN-600

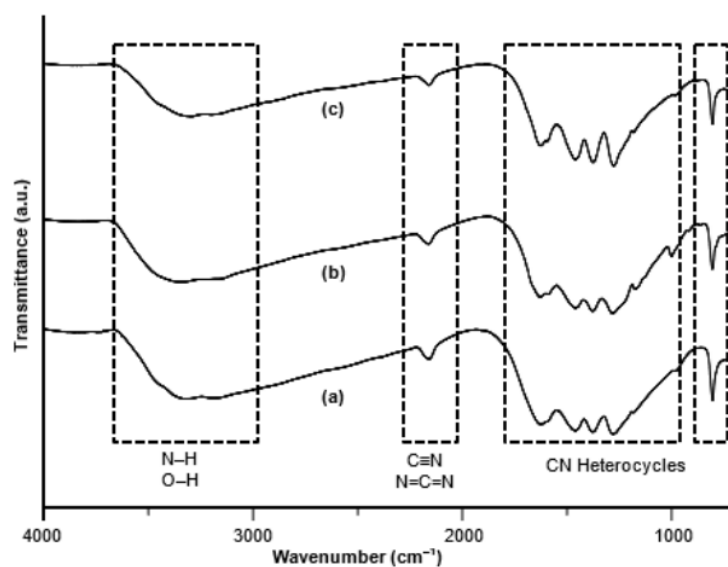


Fig 4. FTIR spectra of (a) CN-500, (b) CN-550, and (c) CN-600

of void channels along with the ABA stacking of poly(triazine imide). Meanwhile, broad bands at around 3000–3700 cm^{-1} were originated from the overlapping of primary amine and secondary amine, N-H and hydroxide, O-H groups, respectively. However, it was

observed that the intensity of the broad peak that attributed to the stretching modes of the primary and secondary amines and their intermolecular hydrogen-bonding interactions (3000–3700 cm^{-1}) reduced as the temperature increased, which especially could be

observed on the CN-600 (Fig. 4(c)). This result suggested that the final condensation product obtained in high temperature was lacking in terminal unreacted $-NH_2$ groups and was cohesive owing to the effect of covalent interactions.

The textural properties and specific surface area were investigated via nitrogen adsorption-desorption analysis. The isotherms and Barrett-Joyner-Halenda (BJH) pore size distribution (inset) of prepared CN-T samples are presented in Fig. 5. All samples showed the type IV isotherm with type H3 hysteresis loop according to IUPAC classification, suggesting the formation of the porous structure. The Brunauer-Emmett-Teller (BET) specific surface areas of the CN-500, the CN-550, and the CN-600 were 24, 73, and $65 \text{ m}^2 \text{ g}^{-1}$, respectively. From the BET specific surface area values obtained, it could be suggested that increasing the synthesis temperature from 500 to 550 °C increased the specific surface area. However, the further increase to 600 °C caused a slight decrease in the value of the specific surface area.

The slight decrease in the surface area of the CN-600 might be due to the hybrid composition of heptazine-based CN and poly(triazine imide). On the other hand, the CN-500 and the CN-600 showed a non-uniform pore size distribution (inset), while the CN-550 showed a uniform pore size distribution as only one sharp and intense peak was observed. Taking account of the most intense and sharp peak, the average pore size diameters for the CN-500, the CN-550, and the CN-600 were determined to be 3.62, 3.63, and 3.62 nm, respectively.

On the contrary, the average pore volume of the CN-500, the CN-550, and the CN-600 were 0.06, 0.23, and $0.19 \text{ cm}^3 \text{ g}^{-1}$, respectively. It could be seen that the low specific surface area of CN-500 was due to low pore volume. The CN-600 showed a slight decrease in its surface area, which could be associated with its decreased pore volume. Besides, the slight decrease in the specific surface area of the CN-600 might be related to the structural changes of the poly(triazine imide) to the hybrid composition of poly(triazine imide) and heptazine

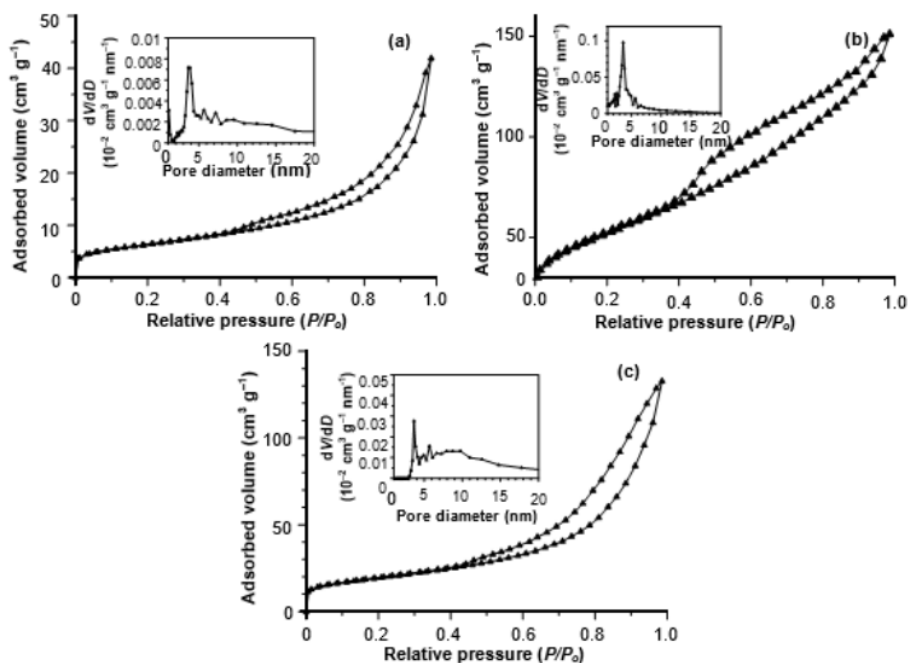


Fig 5. Nitrogen adsorption-desorption isotherms and their respective BJH pore size distribution curves (inset) of (a) CN-500, (b) CN-550, and (c) CN-600

units, considering that the amorphous phase tends to reduce the surface area of the material.

Table 1 shows the percentage of phenol degradation on the prepared CN-*T* samples after 6 h of irradiation under solar light. The CN-500, the CN-550, and the CN-600 showed the photocatalytic activity of 7, 24, and 20%, respectively. The low photocatalytic activity (7%) obtained on the CN-500 sample was clearly due to its large band gap energy, very low crystallinity, and low specific surface area. These properties were mainly due to incomplete polymerization and less condensed structure of CN when synthesized at 500 °C. Meanwhile, the high photocatalytic activity achieved on the CN-550 (24%) was due to its crystallinity and high surface area and might also be associated with the band gap energy value. It could be proposed here that material with a high crystalline phase could lead to an efficient electron charge transfer and provide more active sites for the reaction of photocatalytic oxidation-reduction to occur. On the other hand, the photocatalytic performance of the CN-600 was slightly dropped (20%). As compared to the CN-500 °C, the CN-600 exhibited high photocatalytic activity due to its crystallinity, surface area, and mainly due to its low band gap energy. However, when compared to CN-550 °C, the slightly decreased photocatalytic activity would be due to the decrease in the crystallinity and specific surface area. The decreased band gap energy value of the CN-600 than the CN-550 could not help improving the activity due to such a decrease in crystallinity and surface area. These results demonstrated that the respective chemical and physical properties (crystallinity, band gap energy, and surface area) were significantly dependent on each other. Controlling the synthesis temperature to maintain the chemical and physical properties is needed so that the high photocatalytic performance could be obtained.

Effect of Synthesis Time

The X-ray diffractometer was used to study the structural properties of the prepared CN-*t* samples. The XRD patterns of the prepared CN-2H, CN-4H, and CN-6H were presented in Fig. 6. The two major peaks at a diffraction angle of 2θ of ca. 26.9 (002) and 11.9° (100) were referred to an interlayer distance of graphite-like CN and in-plane arrangement of nitrogen-linked heptazine and/or poly(triazine imide) units [8-19,24-31]. It was clear that all samples showed crystalline properties as the planes of (110), (200), (102), and (210) were observed [15-16,25-26].

As shown in Fig. 6(a) and (b), increasing synthesis time from 2 to 4 h increased the crystallinity of the CN. However, a further increase in the synthesis temperature to 6 h resulted in the reduced peak intensity (Fig. 6(c)). The low crystallinity on sample CN-2H might indicate the polymerization or condensation process of CN was not sufficient at a short synthesis time. However, when the synthesis time was prolonged to 4 h, the supersaturation of the salt melt was high and thus, induced the crystallization process as well as forming a more condensed product. The decrease in the peak intensity on the CN-6H sample could be due to the competition between the crystal growth and the dissolution. It was also believed that prolong the synthesis temperature might cause the CN to be partially decomposed. From the XRD patterns, it can be concluded that 4 h was the optimum reaction time required to synthesize crystalline CN with the high crystalline phase.

The optical properties of the prepared CN-*t* photocatalysts were investigated by the DR UV-vis spectrophotometer. The DR UV-vis spectra of the CN-2H, the CN-4H, and the CN-6H are presented in Fig. 7. For all samples, three absorption peaks corresponded to

Table 1. Properties and percentage of phenol degradation after 6 h under solar light irradiation for CN-*T* samples

| Sample | Crystallinity | E_g^1 (eV) | S.A ² (m ² g ⁻¹) | Degradation (%) |
|--------|---------------|--------------|--|-----------------|
| CN-500 | × | 3.02 | 24 | 7 |
| CN-550 | ✓ | 2.82 | 73 | 24 |
| CN-600 | ✓ | 2.72 | 65 | 20 |

¹Band gap energy values were determined via the Tauc plot

²Specific surface area was determined via the BET technique

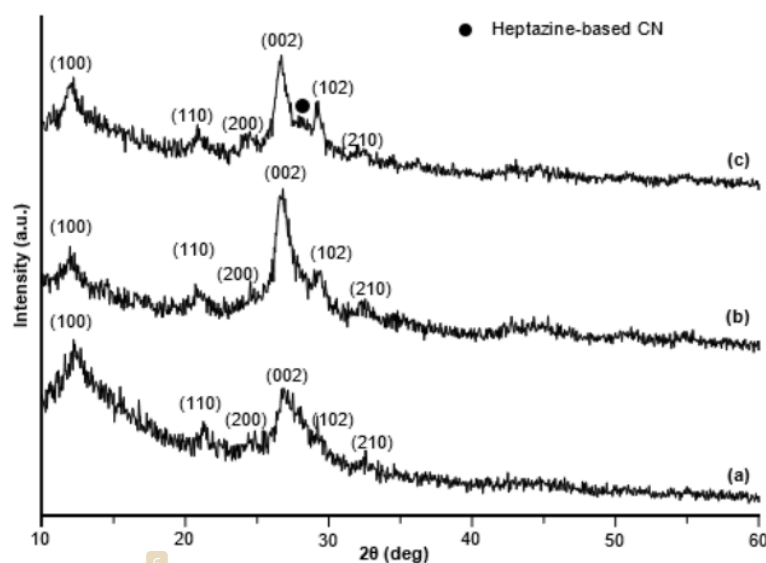


Fig 6. XRD patterns of (a) CN-2H, (b) CN-4H, and (c) CN-6H

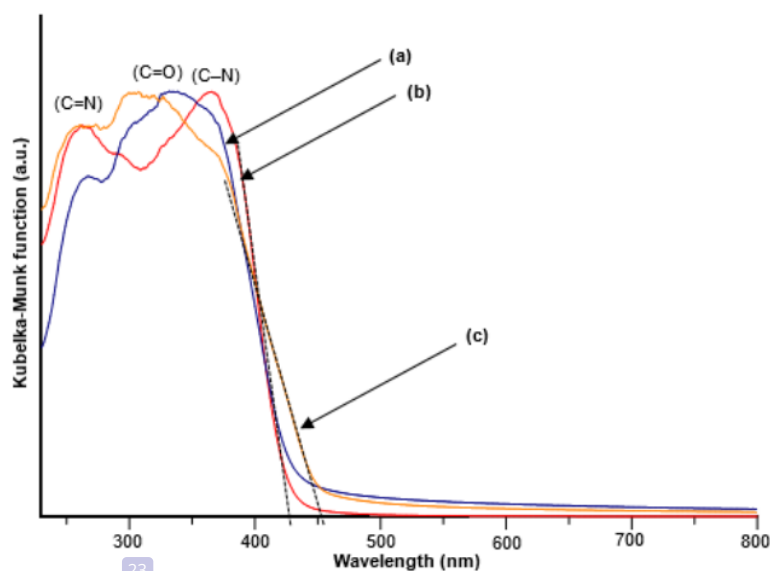


Fig 7. DR UV-vis spectra of (a) CN-2H, (b) CN-4H, and (c) CN-6H

the functional groups of C=N, C=O, and C-O were observed at *ca.* 263, 305, and 360 nm, respectively. Each peak corresponded to $\pi \rightarrow \pi^*$, $\pi \rightarrow \pi^*$ and $n \rightarrow \pi^*$, and $\pi \rightarrow \pi^*$ transitions [8,29-31]. It was observed that the peak of C-N was slightly shifted to a shorter wavelength for the

CN-2H. Due to its less condensed and incomplete polymerization, the CN-2H showed a reduced peak intensity, which belonged to the functional group of C=N. The less condensed product of CN might be caused by the short reaction time. While the CN-2H and the CN-

4H have a similar visible light absorption up to 430 nm, the CN-6H showed a slightly shifted absorption toward longer wavelength in the region up to 460 nm. The slight increase in the visible light absorption on sample CN-6H might be due to better crystallinity or CN framework arrangement, as depicted in Fig. 7(c). The enhanced visible light absorption was also due to the increment in the crystallite size owing to the additional formation of heptazine-based units within the CN-6H sample.

Fig. 8 shows the Tauc plots of the CN-2H, the CN-4H, and the CN-6H samples. The estimated band gap energy values for each respective sample were 2.90, 2.87, and 2.76 eV. These band gap values were in good agreement with crystalline CN as reported elsewhere using similar precursor except for the synthesis procedure [27]. While the CN-2H and CN-4H gave a close value to each other, the CN-6H showed a lower band gap energy. The decrease in its band gap energy could be associated with the increase in its crystallite size or quantum size effect. The increased crystallite size was occurred due to phase changes from poly(triazine imide) to the hybrid composition of heptazine-based and poly(triazine imide). These results suggested the need for optimum synthesis time in preparing crystalline CN as shortening the

synthesis time would result in less condensed CN while lengthening the reaction time might cause structural and phase changes of the CN.

The characteristics of chemical bonds and functional groups of the prepared CN-*t* photocatalysts were analyzed by FTIR spectrophotometer. Fig. 9 shows the FTIR spectra of the CN-2H, the CN-4H, and the CN-6H samples. The formation of CN heterocycles (heptazine and/or poly(triazine imide)) can be observed in both region at *ca.* 810 and 1200–1700 cm^{-1} [8,11,15,17-20,24-26,28]. The wide and broad peaks at *ca.* 3000–3700 cm^{-1} were originated from the overlapping functional groups of N-H and O-H. The presence of the O-H functional group was due to absorbed water molecules at the ambient pressure. The band at *ca.* 810 cm^{-1} corresponded to the bending mode of out-of-plane heptazine-based and/or poly(triazine imide) units. The bands at 1200–1700 cm^{-1} were attributed to the stretching mode of heptazine and/or poly(triazine imide) units.

The small and intense peak appeared at *ca.* 2170 cm^{-1} on all samples indicated the formation of C≡N and N=C=N that were typical for crystalline CN. The formation of both functional groups was due to the broken of the CN continuity networks [8,15,28], owing to

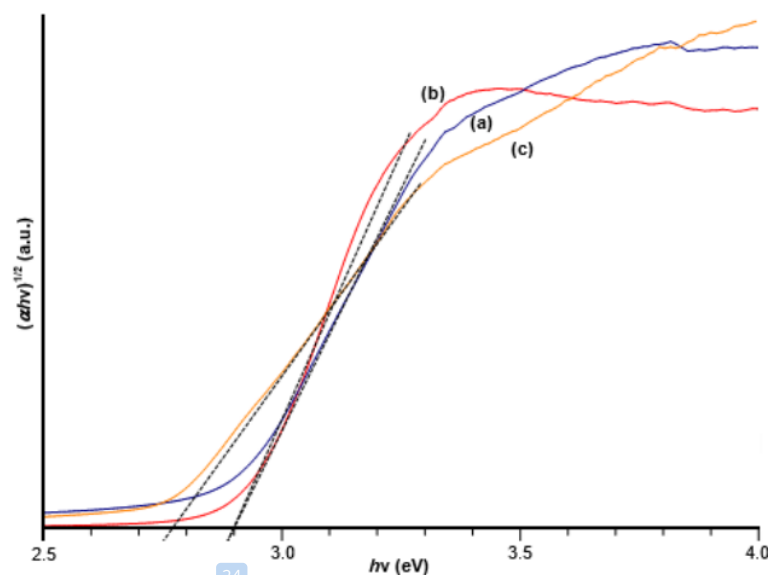


Fig 8. Tauc plots of (a) CN-2H, (b) CN-4H, and (c) CN-6H

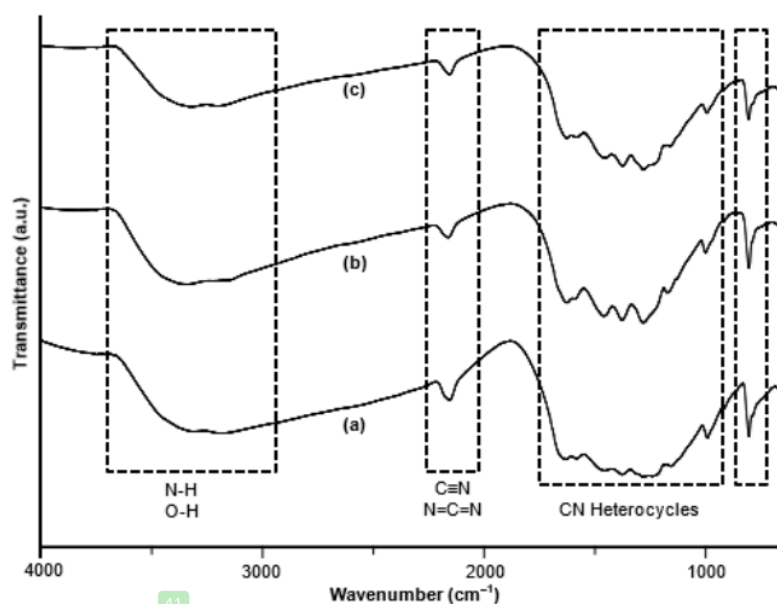


Fig 9. FTIR spectra of (a) CN-4H, (b) CN-6H, and (c) CN-6H

the intercalation of lithium and chloride ions. From the spectra, it can be observed that the less intense peaks of CN heterocycles in the region of 1200–1700 cm^{-1} for the CN-2H sample (Fig. 9(a)) suggested the incomplete formation or less condensed of CN networks due to a short synthesis time. Moreover, increasing synthesis time from 4 to 6 h showed that the CN network structure was decomposed as the peak intensity attributed to CN heterocycles was decreased (Fig. 9(c)). These results demonstrated that short reaction time caused the incomplete formation of CN, while long synthesis time may cause the decomposition of the CN.

The textural properties of the prepared CN-*t* samples were studied via nitrogen adsorption-desorption analysis. The isotherms of each prepared photocatalyst are shown in Fig. 10, while the BJH pore size distribution was shown in the inset of each figure. All samples showed the type IV isotherm with the H3 hysteresis loop, suggesting the presence of the porous structure. From the values of BET specific surface area, increasing synthesis time from 2 to 4 h resulted in the noteworthy increase of the specific surface area from 30 to 73 $\text{m}^2 \text{g}^{-1}$, while further

increment of synthesis time to 6 h caused the specific surface area was slightly dropped to 55 $\text{m}^2 \text{g}^{-1}$.

The low surface area on the CN-2H sample was due to less condensed or incomplete polymerization of CN. This suggested that 4 h of synthesis time was the optimum time to form a highly condensed CN product. In addition, the slightly reduced surface area when prolonging the synthesis time was due to the formation of the hybrid heptazine-based and poly(triazine imide) unit. A similar result was also reported when structural and composition changes were observed [27]. From the insets of the figure, the BJH pore size distribution analysis showed that all samples were uniformly porous with the average sizes of 3.83, 3.62, and 3.62 nm for the CN-2H, the CN-4H, and the CN-6H, respectively. Meanwhile, the average pore volumes calculated via the BJH equation were 0.06, 0.23, and 0.1 $\text{cm}^3 \text{g}^{-1}$, respectively. The difference in the pore size between the CN-2H and both the CN-4H and the CN-6H might be due to the limited growth of crystalline CN that was associated with less condensed and incomplete polymerization process.

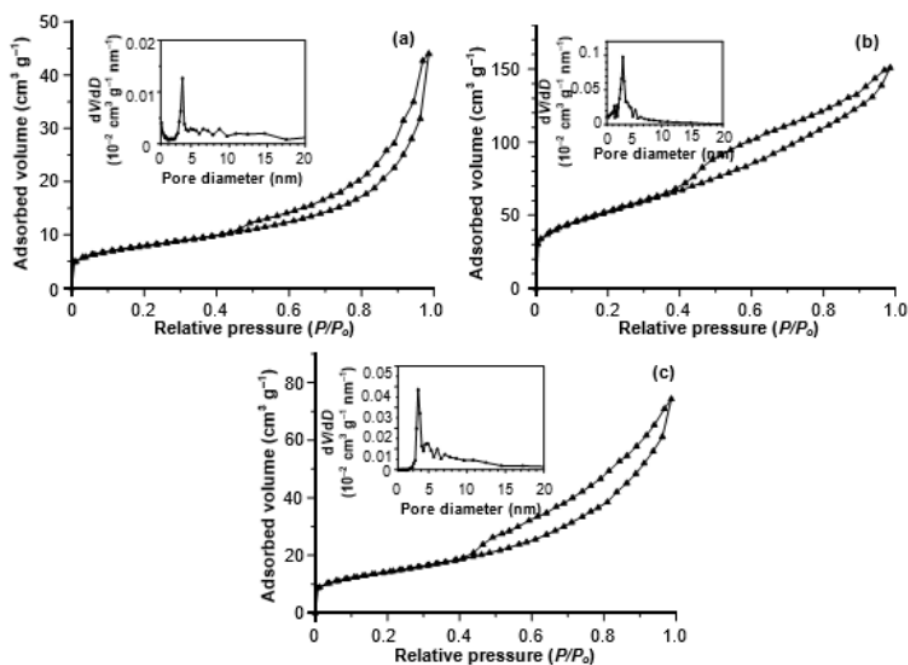


Fig 10. Nitrogen adsorption-desorption isotherms and their respective BJH pore size distribution curves (inset) of (a) CN-2H, (b) CN-4H, and (c) CN-6H

Table 2. Properties and percentage of phenol degradation after 6 hours under solar simulator irradiation for CN-*t* samples

| Sample | Crystallinity ¹ (%) | E_g^2 (eV) | S.A ³ (m ² g ⁻¹) | Degradation (%) |
|--------|--------------------------------|--------------|--|-----------------|
| CN-2H | 86 | 2.90 | 30 | 17 |
| CN-4H | 100 | 2.82 | 73 | 24 |
| CN-6H | 90 | 2.76 | 55 | 20 |

¹Percentage of crystallinity was calculated via the following formula: Crystallinity (%) = (total area of crystalline peaks)/(total area of all peaks). The percentage of crystallinity of sample CN-4H was taken into account as 100%

²Band gap energy values were determined via the Tauc plot

³Specific surface areas were determined via the BET technique

Table 2 lists the chemical and physical properties and photocatalytic activity of the CN-*t* samples after 6 h irradiation under solar light. As shown in the table, the high photocatalytic activity was achieved on the CN-4H sample with 24% of phenol degradation within 6 h of irradiation, while the CN-2H and the CN-6H samples showed phenol degradation of 17 and 20%, respectively. Increasing the synthesis time from 2 to 4 h resulted in the lower band gap energy. However, the photocatalytic activity of the CH-6H did not further increase since the surface

area decreased from 73 to 55%. The high photocatalytic activity obtained by CN-4H sample compared to CN-2H and CN-6H was coming from the crystallinity of the materials, suitable band gap energy, and high surface area. These results suggested that the synthesis time affected the properties of crystallinity, band gap energy, and surface area. Synthesis time of 4 h was important to obtain a CN sample with improved crystallinity, suitable low band gap energy while maintaining the high surface area to achieve a photocatalyst with high activity.

Optimized Synthesis Temperature and Time

As shown in Table 1 and 2, the optimized synthesis temperature and time that gave optimized photocatalytic activity were 550 °C and 4 h, respectively. Both optimization studies showed that the best photocatalytic activity was obtained when the CN has good crystallinity, enough low band gap energy, and high specific surface area. In order to study the morphology of the crystalline CN obtained under these optimized synthesis conditions, the TEM image was recorded and shown in Fig. 11. It was obvious that the prepared crystalline CN gave a near-hexagonal prismatic crystallite with a size of about 50 nm. This morphology was certainly different from the reported spherical shape or worm structures of the amorphous bulk or mesoporous CN [8].

As we compare the photocatalytic activity of the crystalline CN to the TiO₂ P25 as the benchmark photocatalyst so far [2], the performance of the crystalline CN to degrade phenol could be considered low. However, the activity of the TiO₂ P25 is mainly generated under UV light irradiation, which would be one of the limitations to fully utilize the solar light spectrum. On the other hand, while the crystalline CN could be activated by visible light, its efficiency still needs to be improved. In this work, a clear enhancement in the photocatalytic activity could be achieved, where up to 3.4 times higher degradation percentage was obtained on the crystalline CN synthesized under optimized temperature and time as

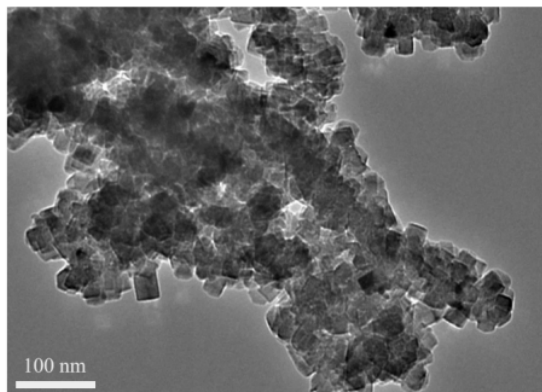


Fig 11. TEM image of crystalline CN prepared at 550 °C and 4 h

compared to the ones synthesized under non-optimized conditions. Such improvement was comparable to the reported approach to increase the photocatalytic activity of the amorphous CN, for example, by modifying the interfacial charge transfer of the amorphous CN by reduced graphene oxide, which gave about 2.8 times better performance for photocatalytic degradation of phenol [31]. This study clearly showed that optimizing the synthesis method is an important strategy to optimize the performance of the photocatalyst.

CONCLUSION

Crystalline CN materials were successfully synthesized at various temperatures (500–600 °C) and various synthesis time (4–6 h). Judging from the photocatalytic performance, the best parameters for synthesis temperature and time were 550 °C and 4 h, respectively. The characterizations by XRD, DR UV-vis, and surface area analyzer revealed that these parameters led to the high crystallinity, enough low band gap energy (2.82 eV), and high specific surface area (73 m² g⁻¹), which resulted in up to 3.4 times higher percentage of phenol degradation than the ones synthesized under the non-optimized synthesis conditions.

ACKNOWLEDGMENTS

Support from the Directorate General of Strengthening Research and Development, Ministry of Research, Technology, and Higher Education of the Republic of Indonesia via the Fundamental Research scheme (PD 2019, No. 058/SP2H/LT/MONO/L7/2019 and No. 001/MACHUNG/LPPM/SP2H-LIT-MONO/III/2019) is greatly acknowledged.

REFERENCES

- [1] Villegas, L.G.C., Mashhadi, N., Chen, M., Mukherjee, D., Taylor, K.E., and Biswas, N., 2016, A short review of techniques for phenol removal from wastewater, *Curr. Pollut. Rep.*, 2 (3), 157–167.
- [2] Barka, N., Bakas, I., Qourzal, S., Assabbane, A., and Ait-Ichou, Y., 2013, Degradation of phenol in water by titanium dioxide photocatalysis, *Orient. J. Chem.*, 29 (3), 1055–1060.

- [3] Fajriati, I., Mudasir, and Wahyuni, E.T., 2014, Photocatalytic decolorization study of methyl orange by TiO₂-chitosan nanocomposites, *Indones. J. Chem.*, 14 (3), 209–218.
- [4] Yuliati, L., Roslan, N.A., Siah, W.R., and Lintang, H.O., 2017, Cobalt oxide-modified titanium dioxide nanoparticle photocatalyst for degradation of 2,4-dichlorophenoxyacetic acid, *Indones. J. Chem.*, 17 (2), 284–290.
- [5] Kunarti, E.S., Kartini, I., Syoufian, A., and Widyandari, K.M., 2018, Synthesis and photoactivity of Fe₃O₄/TiO₂-Co as a magnetically separable visible light responsive photocatalyst, *Indones. J. Chem.*, 18 (3), 403–410.
- [6] Vianney, Y.M., Rosalyn, I., and Angela, S., 2018, Solar based photocatalytic decolorization of four commercial reactive dyes utilizing bound TiO₂-Fe₃O₄ nanocomposite, *Indones. J. Chem.*, 18 (4), 621–631.
- [7] Khoriah, K., Wellia, D.V., Gunlazuardi, J., and Safni, S., 2020, Photocatalytic degradation of commercial diazinon pesticide using C,N-codoped TiO₂ as photocatalyst, *Indones. J. Chem.*, 20 (3), 587–596.
- [8] Lee, S.C., Lintang, H.O., and Yuliati, L., 2012, A urea precursor to synthesize carbon nitride with mesoporosity for enhanced activity in the photocatalytic removal of phenol, *Chem. Asian J.*, 7 (9), 2139–2144.
- [9] Wang, Y., Wang, X., and Antonietti, M., 2012, Polymeric graphitic carbon nitride as a heterogeneous organocatalyst: From photochemistry to multipurpose catalysis to sustainable chemistry, *Angew. Chem. Int. Ed.*, 51 (1), 68–89.
- [10] Zhang, Y., Liu, J., Wu, G., and Chen, W., 2012, Porous graphitic carbon nitride synthesized via direct polymerization of urea for efficient sunlight-driven photocatalytic hydrogen production, *Nanoscale*, 4 (17), 5300–5303.
- [11] Zhao, Y., Zhao, F., Wang, X., Xu, C., Zhang, Z., Shi, G., and Qu, L., 2014, Graphitic carbon nitride nanoribbons: Graphene-assisted formation and synergic function for highly efficient hydrogen evolution, *Angew. Chem. Int. Ed.*, 53 (50), 13934–13939.
- [12] Zhu, J., Xiao, P., Li, H., and Carabineiro, S.A.C., 2014, Graphitic carbon nitride: Synthesis, properties, and applications in catalysis, *ACS Appl. Mater. Interfaces*, 6 (19), 16449–16465.
- [13] Cui, Y., Huang, J., Fu, X., and Wang, X., 2012, Metal-free photocatalytic degradation of 4-chlorophenol in water by mesoporous carbon nitride semiconductors, *Catal. Sci. Technol.*, 2 (7), 1396–1402.
- [14] Zheng, Y., Liu, J., Liang, J., Jaroniec, M., and Qiao, S.Z., 2012, Graphitic carbon nitride materials: Controllable synthesis and applications in fuel cells and photocatalysis, *Energy Environ. Sci.*, 5 (5), 6717–6731.
- [15] Hatta, M.H.M., Lintang, H.O., Lee, S.L., and Yuliati, L., 2019, Synthesis of highly active crystalline carbon nitride prepared in various salt melts for photocatalytic degradation of phenol, *Turk. J. Chem.*, 43, 63–72.
- [16] Bhunia, M.K., Yamauchi, K., and Takanabe, K., 2014, Harvesting solar light with crystalline carbon nitrides for efficient photocatalytic hydrogen evolution, *Angew. Chem. Int. Ed.*, 53 (41), 11001–11005.
- [17] Huang, S., Xu, Y., Ge, F., Tian, D., Zhu, X., Xie, M., Xu, H., and Li, H., 2019, Tailoring of crystalline structure of carbon nitride for superior photocatalytic hydrogen evolution, *J. Colloid Interface Sci.*, 556, 324–334.
- [18] Li, Y., Zhang, D., Feng, X., and Xiang, Q., 2020, Enhanced photocatalytic hydrogen production activity of highly crystalline carbon nitride synthesized by hydrochloric acid treatment, *Chin. J. Catal.*, 41 (1), 21–30.
- [19] Wang, L., Hong, Y., Liu, E., Wang, Z., Chen, J., Yang, S., Wang, J., Lin, X., and Shi, J., 2020, Rapid polymerization synthesizing high-crystalline g-C₃N₄ towards boosting solar photocatalytic H₂ generation, *Int. J. Hydrogen Energy*, 45 (11), 6425–6436.
- [20] Shalom, M., Inal, S., Fettkenhauer, C., Neher, D., and Antonietti, M., 2013, Improving carbon nitride photocatalysis by supramolecular preorganization of monomers, *J. Am. Chem. Soc.*, 135 (19), 7118–7121.

- [21] Prins, L.J., Reinhoudt, D.N., and Timmerman, P., 2001, Noncovalent synthesis using hydrogen bonding, *Angew. Chem. Int. Ed.*, 40 (13), 2382–2426.
- [22] Seto, C.T., Mathias, J.P., and Whitesides, G.M., 1993, Molecular self-assembly through hydrogen bonding: Aggregation of five molecules to form a discrete supramolecular structure, *J. Am. Chem. Soc.*, 115 (4), 1321–1329.
- [23] Çelik, V., and Mete, E., 2012, Range-separated hybrid exchange-correlation functional analyses of anatase TiO₂ doped with W, N, S, W/N, or W/S, *Phys. Rev. B: Condens. Matter*, 86, 205112.
- [24] Lin, L., Yu, Z., and Wang, X., 2018, Crystalline carbon nitride semiconductors for photocatalytic water splitting, *Angew. Chem. Int. Ed.*, 58 (19), 6164–6175.
- [25] Bojdys, M.J., Müller, J.O., Antonietti, M.A., and Thomas, A., 2008, Ionothermal synthesis of crystalline, condensed, graphitic carbon nitride, *Chem. Eur. J.*, 14 (27), 8177–8182.
- [26] Fettkenhauer, C., Weber, J., Antonietti, M., and Dontsova, D., 2014, Novel carbon nitride composites with improved visible light absorption synthesized in ZnCl₂-based salt melts, *RSC Adv.*, 4 (77), 40803–40811.
- [27] Jin, A., Jia, Y., Chen, C., Liu, X., Jiang, J., Chen, X., and Zhang, F., 2017, Efficient photocatalytic hydrogen evolution on band structure tuned polytriazine/heptazine based carbon nitride heterojunctions with ordered needle-like morphology achieved by an in situ molten salt method, *J. Phys. Chem. C*, 121 (39), 21497–21509.
- [28] Liu, J., Zhang, T., Wang, Z., Dawson, G., and Chen, W., 2011, Simple pyrolysis of urea into graphitic carbon nitride with recyclable adsorption and photocatalytic activity, *J. Mater. Chem.*, 21 (38), 14398–14401.
- [29] Sam, M.S., Lintang, H.O., Sanagi, M.M., Lee, S.L., and Yuliati, L., 2014, Mesoporous carbon nitride for adsorption and fluorescence sensor of N-nitrosopyrrolidine, *Spectrochim. Acta, Part A*, 124, 357–364.
- [30] Alim, N.S., Lintang, H.O., and Yuliati, L., 2015, Fabricated metal-free carbon nitride characterizations for fluorescence chemical sensor of nitrate ions, *Jurnal Teknologi*, 76 (13), 1–6.
- [31] Tiong, P., Lintang, H.O., Endud, S., and Yuliati, L., 2015, Improved interfacial charge transfer and visible light activity of reduced graphene oxide-graphitic carbon nitride photocatalysts, *RSC Adv.*, 5 (114), 94029–94039.

23%
SIMILARITY INDEX

8%
INTERNET SOURCES

22%
PUBLICATIONS

3%
STUDENT PAPERS

PRIMARY SOURCES

- 1 Muhammad Cholid Djunaidi, Nabilah Anindita Febriola, Abdul Haris. "Molecularly imprinted membrane for transport of urea, creatinine, and vitamin B as a hemodialysis candidate membrane ", Open Chemistry, 2021
Publication 1%
- 2 repository.machung.ac.id
Internet Source 1%
- 3 Wynona A. Nimpoeno, Hendrik O. Lintang, Leny Yuliati. "Methyl red dye-sensitized zinc oxide as photocatalyst for phenol degradation under visible light", AIP Publishing, 2020
Publication 1%
- 4 Fan Dong, Meiya Ou, Yanke Jiang, Sen Guo, Zhongbiao Wu. "Efficient and Durable Visible Light Photocatalytic Performance of Porous Carbon Nitride Nanosheets for Air Purification", Industrial & Engineering Chemistry Research, 2014
Publication 1%

5

Wee-Jun Ong, Lling-Ling Tan, Yun Hau Ng, Siek-Ting Yong, Siang-Piao Chai. " Graphitic Carbon Nitride (g-C N)-Based Photocatalysts for Artificial Photosynthesis and Environmental Remediation: Are We a Step Closer To Achieving Sustainability? ", Chemical Reviews, 2016

Publication

1 %

6

Fan Dong, Zaiwang Zhao, Ting Xiong, Zilin Ni, Wendong Zhang, Yanjuan Sun, Wing-Kei Ho. " In Situ Construction of g-C N /g-C N Metal-Free Heterojunction for Enhanced Visible-Light Photocatalysis ", ACS Applied Materials & Interfaces, 2013

Publication

1 %

7

Ailing Jin, Yushuai Jia, Changfeng Chen, Xin Liu, Junzhe Jiang, Xiangshu Chen, Fei Zhang. "Efficient Photocatalytic Hydrogen Evolution on Band Structure Tuned Polytriazine/Heptazine Based Carbon Nitride Heterojunctions with Ordered Needle-like Morphology Achieved by an In Situ Molten Salt Method", The Journal of Physical Chemistry C, 2017

Publication

1 %

8

cpk-front-devel.mzk.cz

Internet Source

1 %

9

Faisal Hussin, Hendrik O. Lintang, Siew Ling Lee, Leny Yuliati. "Photocatalytic synthesis of reduced graphene oxide-zinc oxide: Effects of light intensity and exposure time", Journal of Photochemistry and Photobiology A: Chemistry, 2017

Publication

1 %

10

Hongqi Sun, Guanliang Zhou, Yuxian Wang, Alexandra Suvorova, Shaobin Wang. "A New Metal-Free Carbon Hybrid for Enhanced Photocatalysis", ACS Applied Materials & Interfaces, 2014

Publication

1 %

11

Manas K. Bhunia, Kazuo Yamauchi, Kazuhiro Takanabe. "Harvesting Solar Light with Crystalline Carbon Nitrides for Efficient Photocatalytic Hydrogen Evolution", Angewandte Chemie, 2014

Publication

1 %

12

Peggy Tiong, Hendrik O. Lintang, Salasiah Endud, Leny Yuliati. "Improved interfacial charge transfer and visible light activity of reduced graphene oxide-graphitic carbon nitride photocatalysts", RSC Advances, 2015

Publication

1 %

13

Shaowen Cao, Jingxiang Low, Jiaguo Yu, Mietek Jaroniec. "Polymeric Photocatalysts

<1 %

Based on Graphitic Carbon Nitride", Advanced Materials, 2015

Publication

14

Zhenzhen Lu, Dong Liu, Jianting Zhou, Fan Dong. "Lower treating temperature leading to higher air purification activity", Chemical Engineering Journal, 2017

Publication

<1 %

15

Shu Chin Lee, Hendrik O Lintang, Leny Yuliati. " High photocatalytic activity of Fe O /TiO nanocomposites prepared by photodeposition for degradation of 2,4-dichlorophenoxyacetic acid ", Beilstein Journal of Nanotechnology, 2017

Publication

<1 %

16

Hongmei Wang, Wei Zhou, Peng Li, Xin Tan, Yanyu Liu, Wenping Hu, Jinhua Ye, Tao Yu. "Enhanced Visible-Light-Driven Hydrogen Production of Carbon Nitride by Band Structure Tuning", The Journal of Physical Chemistry C, 2018

Publication

<1 %

17

Hossein Rasoulnezhad, Ghassem Kavei, Kamran Ahmadi, Mohammad Reza Rahimipour. "Visible light photocatalytic degradation of paraoxon and parathion pesticides on carbon-doped TiO₂ nanorod

<1 %

thin films", Journal of Materials Science:
Materials in Electronics, 2017

Publication

18

bioresources.cnr.ncsu.edu

Internet Source

<1 %

19

www.mdpi.com

Internet Source

<1 %

20

www.hindawi.com

Internet Source

<1 %

21

Qing Han, Bing Wang, Jian Gao, Zhihua Cheng,
Yang Zhao, Zhipan Zhang, Liangti Qu. "

Atomically Thin Mesoporous Nanomesh of
Graphitic C N for High-Efficiency
Photocatalytic Hydrogen Evolution ", ACS
Nano, 2016

Publication

<1 %

22

Ruiru Zhao, Jianping Gao, Shunkang Mei,
Yongli Wu, Xiaoxue Wang, Xiangang Zhai,
Jiangbing Yang, Chaoyue Hao, Jing Yan. "
Facile synthesis of graphitic C N nanoporous-
tube with high enhancement of visible-light
photocatalytic activity ", Nanotechnology,
2017

Publication

<1 %

23

Leny Yuliati, Peggy Tiong, Hendrik O Lintang.
"Response surface methodology to optimize
the performance of reduced graphene oxide-

<1 %

mesoporous carbon nitride photocatalysts",
Materials Research Express, 2019

Publication

24

Longyan Wang, Yuanzhi Hong, Enli Liu, Xixin Duan, Xue Lin, Junyou Shi. "A bottom-up acidification strategy engineered ultrathin g-C₃N₄ nanosheets towards boosting photocatalytic hydrogen evolution", Carbon, 2020

Publication

25

Jiajia Wang, Lin Tang, Guangming Zeng, Yani Liu, Yaoyu Zhou, Yaocheng Deng, Jingjing Wang, Bo Peng. " Plasmonic Bi Metal Deposition and g-C₃N₄ Coating on Bi WO₆ Microspheres for Efficient Visible-Light Photocatalysis ", ACS Sustainable Chemistry & Engineering, 2016

Publication

26

Xiaochun Gao, Xuejiao Jiao, Lanchun Zhang, Wencai Zhu, Xiaohong Xu, Houyi Ma, Ting Chen. " Cosolvent-free nanocasting synthesis of ordered mesoporous g-C₃N₄ and its remarkable photocatalytic activity for methyl orange degradation ", RSC Advances, 2015

Publication

27

pubs.acs.org
Internet Source

<1 %

<1 %

<1 %

<1 %

28

S. T. Nishanthi, Battula Venugopala Rao, Kamalakannan Kailasam. "Metal-Free Organic Semiconductors for Visible-Light-Active Photocatalytic Water Splitting", Wiley, 2018

Publication

<1 %

29

Zheng, J.. "Effect of preparation methods and mirror plane cation on the catalytic property of AMnAl¹1O¹9-"@d (A=K, Ca) catalysts", Catalysis Communications, 20090330

Publication

<1 %

30

Shao, Leqiang, Deli Jiang, Peng Xiao, Liming Zhu, Suci Meng, and Min Chen. "Enhancement of g-C₃N₄ nanosheets photocatalysis by synergistic interaction of ZnS microsphere and RGO inducing multistep charge transfer", Applied Catalysis B Environmental, 2016.

Publication

<1 %

31

hdl.handle.net

Internet Source

<1 %

32

Xu, Huan-Yan, Li-Cheng Wu, Hang Zhao, Li-Guo Jin, and Shu-Yan Qi. "Synergic Effect between Adsorption and Photocatalysis of Metal-Free g-C₃N₄ Derived from Different Precursors", PLoS ONE, 2015.

Publication

<1 %

33

Sefiu Abolaji Rasaki, Hangjia Shen, Tiju Thomas, Minghui Yang. "Solid-Solid

<1 %

Separation Approach for Preparation of Carbon-Supported Cobalt Carbide Nanoparticle Catalysts for Oxygen Reduction", ACS Applied Nano Materials, 2019

Publication

34

Shuaibu Abdullahi Hudu, Mohd Taib Niazlin, Syafinaz Amin Nordin, Nabil Saad Harmal et al. "Hepatitis E virus isolated from chronic hepatitis B patients in Malaysia: Sequences analysis and genetic diversity suggest zoonotic origin", Alexandria Journal of Medicine, 2017

Publication

<1 %

35

Jae Sung Lee. "Photocatalytic Water Splitting Under Visible Light with Particulate Semiconductor Catalysts", Catalysis Surveys from Asia, 2006

Publication

<1 %

36

Shajahan Shanavas, Selvaraj Mohana Roopan, Arumugam Priyadharsan, Duraipandi Devipriya et al. "Computationally guided synthesis of (2D/3D/2D) rGO/Fe₂O₃/g-C₃N₄ nanostructure with improved charge separation and transportation efficiency for degradation of pharmaceutical molecules", Applied Catalysis B: Environmental, 2019

Publication

<1 %

37

open.library.ubc.ca

Internet Source

<1 %

38

Manas K. Bhunia, Sigismund Melissen, Manas R. Parida, Pradip Sarawade et al. "Dendritic Tip-on Polytriazine-Based Carbon Nitride Photocatalyst with High Hydrogen Evolution Activity", Chemistry of Materials, 2015

Publication

<1 %

39

Shu Chin Lee, Hendrik O. Lintang, Leny Yuliati. "A Urea Precursor to Synthesize Carbon Nitride with Mesoporosity for Enhanced Activity in the Photocatalytic Removal of Phenol", Chemistry - An Asian Journal, 2012

Publication

<1 %

40

Sundararajan Raja, Chinnasamy Rajaram Prakash. "Novel 1-(4-substituted benzylidene)-4-(1-(substituted methyl)-2,3-dioxindolin-5-yl)semicarbazide derivatives for use against Mycobacterium tuberculosis H37Rv (ATCC 27294) and MDR-TB strain", Archives of Pharmacal Research, 2013

Publication

<1 %

41

Yong Wang, Yuan Zhang, Jinghua Wang, Ming Wang, Hongyou Cui, Weiming Yi, Feng Song, Pingping Zhao, Xiuyu Sun, Yujiao Xie. "Temperature-Responsive HCl-Releasing Catalysts for Cellulose Hydrolysis into Glucose", Catalysis Letters, 2020

<1 %

42 Yusong Gao, Guisheng Qi, Wenchao Yan, Da Guo, Weizhou Jiao, Youzhi Liu. "Preparation of L-cysteine modified MnFe₂O₄ nanoparticles based on high-gravity technology and application for the removal of lead", Journal of Environmental Chemical Engineering, 2022
Publication

<1 %

43 ciad.repositorioinstitucional.mx
Internet Source

<1 %

44 donglin.nju.edu.cn
Internet Source

<1 %

45 pure.ulster.ac.uk
Internet Source

<1 %

46 www.matec-conferences.org
Internet Source

<1 %

47 Katsumata, Hideyuki, Tsubasa Sakai, Tohru Suzuki, and Satoshi Kaneco. "Highly Efficient Photocatalytic Activity of g-C₃N₄/Ag₃PO₄ Hybrid Photocatalysts through Z-Scheme Photocatalytic Mechanism under Visible Light", Industrial & Engineering Chemistry Research, 2014.
Publication

<1 %

48 Li, Xiaobo, Gareth Hartley, Antony J. Ward, Pamela Young, Anthony F Masters, and Thomas Maschmeyer. "Hydrogenated Defects

<1 %

in Graphitic Carbon Nitride Nanosheets for Improved Photocatalytic Hydrogen Evolution",
The Journal of Physical Chemistry C

Publication

49

Natalita M. Nursam, Xingdong Wang, Rachel A. Caruso. "High-Throughput Synthesis and Screening of Titania-Based Photocatalysts", ACS Combinatorial Science, 2015

Publication

<1 %

50

Qian Huang, Jiaguo Yu, Shaowen Cao, Can Cui, Bei Cheng. "Efficient photocatalytic reduction of CO₂ by amine-functionalized g-C₃N₄", Applied Surface Science, 2015

Publication

<1 %

51

Satish Laxman Shinde, Satoshi Ishii, Thang Duy Dao, Ramu Pasupathi Sugavaneshwar et al. "Enhanced Solar Light Absorption and Photoelectrochemical Conversion Using TiN Nanoparticle-Incorporated C N -C Dot Sheets", ACS Applied Materials & Interfaces, 2018

Publication

<1 %

52

Wendong Zhang, Qin Zhang, Fan Dong, Zaiwang Zhao. "The Multiple Effects of Precursors on the Properties of Polymeric Carbon Nitride", International Journal of Photoenergy, 2013

Publication

<1 %

53

Xiuna Yu, Zhixiang Liu, Yemei Wang, Hongyu Luo, Xu Tang. " Fabrication of corncob-derived biomass charcoal decorated g-C N photocatalysts for removing 2-mercaptobenzothiazole ", New Journal of Chemistry, 2020

Publication

<1 %

54

Yao Zheng, Jian Liu, Ji Liang, Mietek Jaroniec, Shi Zhang Qiao. "Graphitic carbon nitride materials: controllable synthesis and applications in fuel cells and photocatalysis", Energy & Environmental Science, 2012

Publication

<1 %

55

dokumen.pub

Internet Source

<1 %

56

scholarbank.nus.edu.sg

Internet Source

<1 %

57

spj.sciencemag.org

Internet Source

<1 %

58

"Heterogeneous Catalysts", Wiley, 2021

Publication

<1 %

59

A. Elhalil, R. Elmoubarki, M. Farnane, A. Machrouhi, M. Sadiq, F.Z. Mahjoubi, S. Qourzal, N. Barka. "Photocatalytic degradation of caffeine as a model pharmaceutical pollutant on Mg doped ZnO-Al

<1 %

2 O 3 heterostructure", Environmental Nanotechnology, Monitoring & Management, 2018

Publication

60

Asmat Ali, Muhammad Bilal, Romana Khan, Robina Farooq, Maria Siddique. "Ultrasound-assisted adsorption of phenol from aqueous solution by using spent black tea leaves", Environmental Science and Pollution Research, 2018

Publication

<1 %

61

Isabel Köwitsch, Michael Mehring. "Carbon nitride materials: impact of synthetic method on photocatalysis and immobilization for photocatalytic pollutant degradation", Journal of Materials Science, 2021

Publication

<1 %

62

Jiangpeng Wang, Jingkun Cong, Hui Xu, Jinming Wang, Hong Liu, Mei Liang, Junkuo Gao, Qingqing Ni, Juming Yao. " Facile Gel-Based Morphological Control of Ag/ -C N Porous Nanofibers for Photocatalytic Hydrogen Generation ", ACS Sustainable Chemistry & Engineering, 2017

Publication

<1 %

63

Kevin Reilly, Baizeng Fang, Fariborz Taghipour, David P. Wilkinson. "Simple and Scalable Synthesis of Vertically Aligned Anatase

<1 %

Nanowires for Enhanced Photoelectrochemical Performance", ACS Applied Energy Materials, 2020

Publication

64

Lee, Shu Chin, Norhasnita Hasan, Hendrik O. Lintang, Mustaffa Shamsuddin, and Leny Yuliati. "Photocatalytic removal of 2,4-dichlorophenoxyacetic acid herbicide on copper oxide/titanium dioxide prepared by co-precipitation method", IOP Conference Series Materials Science and Engineering, 2016.

Publication

<1 %

65

Leqiang Shao, Deli Jiang, Peng Xiao, Liming Zhu, Suci Meng, Min Chen. "Enhancement of g-C₃N₄ nanosheets photocatalysis by synergistic interaction of ZnS microsphere and RGO inducing multistep charge transfer", Applied Catalysis B: Environmental, 2016

Publication

<1 %

66

Pengcheng Yan, Jintao Dong, Zhao Mo, Li Xu, Junchao Qian, Jiexiang Xia, Jianming Zhang, Henan Li. "Enhanced photoelectrochemical sensing performance of graphitic carbon nitride by nitrogen vacancies engineering", Biosensors and Bioelectronics, 2020

Publication

<1 %

67

Shaowen Cao, Jiaguo Yu. "g-C₃N₄-Based Photocatalysts for Hydrogen Generation", The Journal of Physical Chemistry Letters, 2014

Publication

<1 %

68

Xiaoyun Chen, Dong-Hau Kuo, Yong-Xuan Hou. "Enhancing the photodegradation of charged pollutants under visible light in Ag₂O/g-C₃N₄ catalyst by Coulombic interaction", Journal of Materials Science, 2017

Publication

<1 %

69

Xie, Meng, Wei Wei, Zhifeng Jiang, Yuanguo Xu, and Jimin Xie. "Carbon nitride nanowires/nanofibers: A novel template-free synthesis from a cyanuric chloride-melamine precursor towards enhanced adsorption and visible-light photocatalytic performance", Ceramics International, 2016.

Publication

<1 %

70

Amanj Kheradmand, Yuxiang Zhu, Wenwen Zhang, Aleksei Marianov, Yijiao Jiang. "Cobalt oxide on mesoporous carbon nitride for improved photocatalytic hydrogen production under visible light irradiation", International Journal of Hydrogen Energy, 2019

Publication

<1 %

71

L Yuliati, S Z M So'ad, N S Alim, H O Lintang. "Fluorescence Sensing of Nitrite Ions on Polyvinylpyrrolidone/Zinc Oxide Composites Prepared by Impregnation Method", IOP Conference Series: Materials Science and Engineering, 2017

Publication

<1 %

72

Qian Wang, Kazunari Domen. "Particulate Photocatalysts for Light-Driven Water Splitting: Mechanisms, Challenges, and Design Strategies", Chemical Reviews, 2019

Publication

<1 %

73

Qiaohui Jia, Sufen Zhang, Xiaoxia Jia, Xiaoyang Dong, Ziwei Gao, Quan Gu. "Photocatalytic coupled redox cycle for two organic transformations over Pd/carbon nitride composites", Catalysis Science & Technology, 2019

Publication

<1 %

74

Yajun Zhou, Lingxia Zhang, Weimin Huang, Qinglu Kong, Xiangqian Fan, Min Wang, Jianlin Shi. "N-doped graphitic carbon-incorporated g-C₃N₄ for remarkably enhanced photocatalytic H₂ evolution under visible light", Carbon, 2016

Publication

<1 %

75

Yanan Li, Min-Qiang Wang, Shu-Juan Bao, Shiyu Lu, Maowen Xu, Dingbiao Long, Shihua

<1 %

Pu. "Tuning and thermal exfoliation graphene-like carbon nitride nanosheets for superior photocatalytic activity", *Ceramics International*, 2016

Publication

76

Zhengyuan Zhang, Deli Jiang, Di Li, Minqiang He, Min Chen. "Construction of SnNb₂O₆ nanosheet/g-C₃N₄ nanosheet two-dimensional heterostructures with improved photocatalytic activity: Synergistic effect and mechanism insight", *Applied Catalysis B: Environmental*, 2016

Publication

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

PAGE 8

PAGE 9

PAGE 10

PAGE 11

PAGE 12

PAGE 13

PAGE 14

PAGE 15
