

Systematic Study of Calcination Temperature on Photocatalytic Activity of Luminescent Copper(I) Pyrazolate Complex/Titanium Oxide Composites

Nurul Husna Sabran^a, Leny Yuliaty^{b-d}, Siew Ling Lee^{a,c}, and Hendrik O. Lintang^{b,c,*}

^a Department of Chemistry, Faculty of Science, Universiti Teknologi Malaysia, Malaysia

^b Department of Chemistry, Faculty of Science and Technology, Universitas Ma Chung, Indonesia

^c Centre for Sustainable Nanomaterials, Universiti Teknologi Malaysia, Malaysia


^d Ma Chung Research Center for Photosynthetic Pigments, Universitas Ma Chung, Indonesia

*Corresponding Author: hendrik.lintang@machung.ac.id (Tlp. +62-341-550171 ; Fax +62-341-550175)

Abstract

Columnar assembly of luminescent 3,5-dimethyl pyrazolate complexes/titanium oxide composites with different metal ions has shown significant improvement in its photocatalytic activity for the removal and degradation of 2, 4-dichlorophenoxyacetic acid (2,4-D). Since photocatalytic activity of semiconductor titanium oxide (TiO₂) with an anatase phase can be improved by calcination temperature, we report the effect of heat treatments on the preparation of copper(I) 3,5-dimethyl pyrazolate complex/titanium oxide composite ([Cu₃Pz₃]/TiO₂) for the removal and degradation of 2,4-D. Photocatalyst composites [Cu₃Pz₃]/TiO₂ were successfully prepared using an impregnation method with different calcination temperature at 373, 473 and 573 K. Although, the activity of photocatalyst composites [Cu₃Pz₃]/TiO₂ was significantly improved with increasing of calcination temperature on pure TiO₂, it was slightly reduced with an increase of calcined temperature to 473 and 573 K. These results showed that [Cu₃Pz₃]/TiO₂ was unstable at high temperature due to the decomposition of molecular structure of [Cu₃Pz₃] during the preparation of the photocatalyst. Hence, suitable calcination temperature is an important parameter to increase photocatalytic activity of photocatalyst composites [Cu₃Pz₃]/TiO₂.

Luminescent composites [Cu₃Pz₃]/TiO₂ enable as a semiconductor photocatalyst with a significant improvement on photocatalytic activity for removal and degradation of 2,4-D. This higher photocatalytic activity compared to TiO₂ is due to the presence of columnar assembly for delaying electron-hole recombination between valance and conduction bands. Indeed, calcination temperature is important parameter to increase photocatalytic activity of photocatalyst composites.

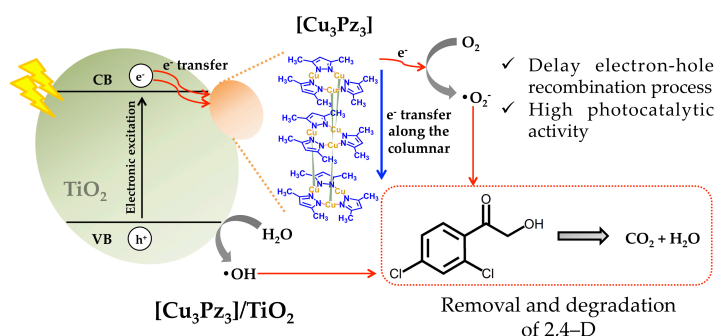

Article History:

Received: 17 August 2019, Revised 21 August 2019, Accepted 22 August 2019, Available Online 31 August 2019

<http://dx.doi.org/10.34311/jics.2019.02.1.54>

Content from this work may be used under the terms of the [Creative Commons Attribution 4.0 license](https://creativecommons.org/licenses/by/4.0/)

Keywords: Calcination, Copper(I) pyrazolate complex, 2,4-Dichlorophenoxyacetic acid

Acknowledgment

The authors thank Penelitian Mandiri (045/MACHUNG/LPPM-LIT-MANDIRI/IV/2018), Universitas Ma Chung, Indonesia, and Transdisciplinary Research Grant (Q.J130000.3554.07G57), Universiti Teknologi Malaysia for financial supports. NHS acknowledges the Ministry of Higher Education, Malaysia for the financial support through MyBrain15 Scholarship (MyPhD).

Introduction

Nowadays, an increasing contamination level in water sources with colorless chlorinated compounds is one of the greatest concern to the human future. Since 1945, 2,4-dichlorophenoxyacetic acid (2,4-D) has been widely used as selective herbicides in agriculture fields for controlling the broadleaf weeds [1,2]. In contrast, this herbicide is relatively high soluble in water and easily flow to water stream. In addition, the degradation rate of 2,4-D also considered slow, which takes few days, depending on some factors such as concentration, acidity, and temperature. Several reports showed that 2,4-D in contaminated water source can be removed using chemical, microbial and photochemical process [3-5]. However, those methods still gave low conversion percentage and take a long time for the removal of 2,4-D. Recently, titanium oxide (TiO₂) with its semiconductor properties has been reported as a promising heterogeneous photocatalyst in water treatment technology due to their high activity, large stability, low price, and nontoxic [6-8].

While a lot of strategies have been developed to improve photocatalytic activity of TiO₂ [9-12], modification using copper complexes have gained such a tremendous attention due to the ability of the composite in improving suppression of electron-hole recombination process, in which the columnar structure from a weak metal-metal interaction can trap the transferred electron along its assembly [13,14]. In 2016, a first modified luminescent trinuclear copper(I) pyrazolate complex/titanium oxide has been reported to give better activity compared to pure TiO₂ [13]. This result highlighted that the presence of luminescent trinuclear copper(I) pyrazolate complex ([Cu₃Pz₃]) with the different molecular structure of reduced electron-hole recombination process and slightly increased photocatalytic activity of TiO₂. In particular, the luminescent composite of copper complex prepared from 3,5-dimethyl pyrazole ligand with a less rigid molecular structure showed higher photocatalytic activity compared to that 4-(3,5-dimethoxybenzyl)-3,5-dimethyl pyrazole ligand. Recently, we also have reported on photocatalytic activity of modified TiO₂ using 3,5-dimethyl pyrazolate complexes with different group 11 metal ions [14]. Such luminescent properties are required not only for indicating the electron-hole recombination from its emission spectral changes, but also for evaluating the

possibility of the electron transfer from conduction band to columnar assembly of the complex.

Although many studies have been done to investigate the performance of pure and modified TiO₂ composites; however, the effect of heat treatment on the activity of luminescent composites has still not yet reported so far. For example, Siah and her co-workers have reported that commercial TiO₂ having anatase phase showed an improvement in the removal and degradation of 2,4-D with increasing of calcination temperature [15]. In contrast, commercial TiO₂ with a combination of anatase and rutile phase possessed different results where the high calcination temperature might change the active site of photocatalyst composites. Therefore, we report on systematic study of luminescent trinuclear copper(I) 3,5-dimethyl pyrazolate complex/titanium oxide photocatalyst composites for the removal and degradation of 2,4-D. In this study, we demonstrated that suitable heat treatment in preparation of TiO₂ composites is also an important parameter to be considered for the improvement of photocatalytic activity.

Experimental Section

Materials and apparatus

Hombikat UV100 TiO₂ (Sachtleben Chemie) was used as a precursor of the anatase phase. [Cu₃Pz₃] was previously synthesized from 3,5-dimethyl pyrazole ligand (Sigma-Aldrich, C₅H₈N₂ as Pz-CH₃, 99%) and a metal salt of tetrakis(acetonitrile)copper(I) hexafluorophosphate (Sigma-Aldrich, C₈H₁₂CuF₆N₄P, 97%) [15,16]. High purity of extra dry tetrahydrofuran, dichloromethane, and methanol from Merck was directly used to synthesize the complex under an inert condition. Freshly distilled triethylamine was firstly prepared in the round bottom flask containing potassium hydroxide (Merck, KOH) under a vacuum and an inert condition using a distillation technique. The freshly distilled triethylamine was directly used for the desired reaction. 2,4-D (Sigma-Aldrich, C₈H₆Cl₂O₃, 98%) was used as a model of organic pollutant in the photocatalytic reaction. Calcination with the temperature of 373, 473 and 573 K and a heating rate of 10 K min⁻¹ under atmospheric conditions was performed using a Nabertherm muffle furnace on a model of LE6/11.

The structure of the samples was characterized using X-ray Diffractometer (XRD) on a model of Bruker D8 with a scan speed of 0.05 °s⁻¹ and Fourier

transform infrared spectroscopy (FT-IR) on a model of Nicolet iS50 Thermo Scientific (potassium bromide with a pellet technique). The morphology of the composites was further studied using field-emission scanning electron microscopy (FE-SEM, JEOL on a model of JSM-6701F).

The photocatalytic reaction was performed on UV light irradiation using 200 W Xe-Hg lamp with 8 mW cm⁻² of light intensity. The photocatalytic activity was evaluated using high-performance liquid chromatography (HPLC) on a model of Shimadzu Prominence LC-20A equipped with UV detector and Hypersil GOLD PFP column (150 × 4.6 mm).

Synthesis of photocatalyst composites

[Cu₃Pz₃]/TiO₂ photocatalyst composites were prepared using an impregnation method where 0.1 weight percent of [Cu₃Pz₃] in dichloromethane solution (25 mL) was mixed with 1.0 g of TiO₂. The mixture was sonicated for 20 minutes for better dispersion [13,16,18]. Then, the solution was stirred until dried at room temperature and calcined at 373 K for 4 hours. The protocol was repeated at different calcination temperatures (473 and 573 K) for both unmodified and modified TiO₂ to study the effect of heat treatment towards the activity.

Photocatalytic study of photocatalyst composites

[Cu₃Pz₃]/TiO₂ photocatalyst composites were tested for degradation of 2,4-D under UV light irradiation [19,20]. Particularly, photocatalyst composite (50 mg) was added to the solution of 2,4-D (50 mL, 0.5 mM) and stirred in a dark condition for 1 hour to reach the adsorption-desorption equilibrium. Then, the mixture was further stirred for 1 hour under the same UV light irradiation. After the adsorption process and UV lamp exposure, the mixture was collected and purified using a nylon membrane filter (0.2 μm). The filtered solution was further analyzed using HPLC. The concentration of 2,4-D was examined with an eluent mixture of acetonitrile/distilled water in 60:40 (v/v) at wavelength of 283 nm. The removal and degradation of 2,4-D were calculated from equations (1) and (2).

$$\text{Removal of 2,4-D} = \frac{[2,4-D]_i - [2,4-D]_f}{[2,4-D]_i} \times 100 \quad (1)$$

$$\text{Degradation of 2,4-D} = \frac{[2,4-D]_i - [2,4-D]_f - [2,4-DCP]}{[2,4-D]_i} \times 100 \quad (2)$$

The concentration of 2,4-D before and after UV light irradiation is denoted as [2,4-D]_i and [2,4-D]_f while the concentration of its intermediate (2,4-dichlorophenol, 2,4-DCP) is denoted as [2,4-DCP]. These equations will provide the calibration curves for the determination of photocatalytic activity.

Results and Discussion

Structural analysis of photocatalyst composites

The molecular structure of [Cu₃Pz₃] and [Cu₃Pz₃]/TiO₂ photocatalyst composites were firstly confirmed by using FT-IR measurement as shown in Figure 1 [16,21]. According to the previous report, vibration bands at 3375 cm⁻¹ (6) and 1626 cm⁻¹ (7) are assigned to O–H group which indicated the presence of moisture. While the vibration band of Ti–O group was observed at the range of 700 to 500 cm⁻¹ (8) [21]. In contrast, although [Cu₃Pz₃] was prepared as a composite with TiO₂, there is no vibration band of [Cu₃Pz₃] in [Cu₃Pz₃]/TiO₂ photocatalyst composites due to the low loading amount of the [Cu₃Pz₃].

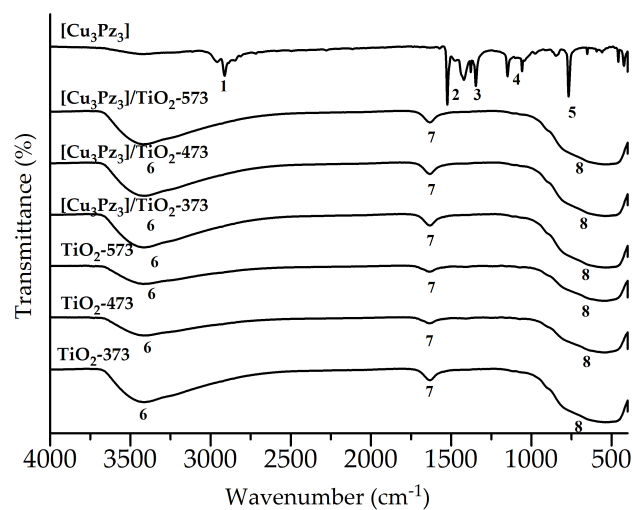


Figure 1. FT-IR spectra of [Cu₃Pz₃] as well as TiO₂ and [Cu₃Pz₃]/TiO₂ at different calcination temperatures.

Figure 2 shows XRD pattern of TiO₂ with 2θ at 25.35°, 38.10°, 48.05°, 54.55° and 62.60° which is related to a standard value of Joint Committee on Powder Diffraction Standards (JCPDS) with the file number of 21-1271. This XRD pattern indicates the presence of an anatase phase for TiO₂ [14,20,22]. Moreover, by using Scherrer equation for the main diffraction peak as shown in Table 1, the estimated crystallite sizes of TiO₂ and [Cu₃Pz₃]/TiO₂ photocatalyst composites were calculated with different calcination temperatures. These results showed that heat treatment slightly affects the

crystallite size of pure TiO₂. In contrast, the addition of [Cu₃Pz₃] has not affected structural properties of the TiO₂ in its composites. Otherwise, crystallite size of TiO₂ compared to the composites can be used to indicate both the presence of their agglomeration and distribution.

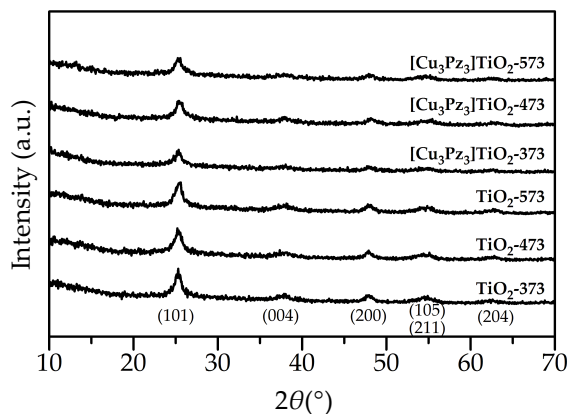


Figure 2. XRD patterns of TiO₂ and [Cu₃Pz₃]/TiO₂ at different calcination temperatures.

Table 1. Analyses crystallite size of TiO₂ and [Cu₃Pz₃]/TiO₂ at different calcination temperatures.

Photocatalyst composites	Crystallite size ¹ (nm)
TiO ₂ -373	9.5
TiO ₂ -473	12.3
TiO ₂ -573	14.8
[Cu ₃ Pz ₃]/TiO ₂ -373	9.6
[Cu ₃ Pz ₃]/TiO ₂ -473	9.8
[Cu ₃ Pz ₃]/TiO ₂ -573	9.7

¹ Calculated using the Scherrer equation.

The morphology of TiO₂ and [Cu₃Pz₃]/TiO₂ was studied using FE-SEM measurement. Based on FE-SEM images in Figure 3, the surface morphology of modified [Cu₃Pz₃]/TiO₂ photocatalyst composites showed almost similar properties to that of TiO₂. These results showed that [Cu₃Pz₃] was dispersed well at the surface of the TiO₂ composites where it was supported by its crystallite size of the composites as shown in Table 1. Moreover, such a small amount of complex will not affect the morphology of the TiO₂ in their composites.

Photocatalytic activity of photocatalyst composites

The performance of TiO₂ and [Cu₃Pz₃]/TiO₂ photocatalyst composites was tested at ambient temperature in 1 hour under UV light irradiation.

Based on stability test under UV light irradiation with [Cu₃Pz₃] only and without photocatalyst, degradation of 2,4-D was not occurred due to lack of hydroxyl radical (\bullet OH). By using the equations 1 and 2 for the calibration curve, the performance of photocatalyst composites can be evaluated for percentages of degradation (conversion of 2,4-D to other compounds, except 2,4-DCP) and removal (decreasing of concentration of 2,4-D). The removal can be used for determination of decreasing of concentration of 2,4-D. The photocatalytic testing results of the [Cu₃Pz₃]/TiO₂-373 photocatalyst composite (Figure 4) showed that addition of [Cu₃Pz₃] was found to give significant highest removal in 96% and degradation in 30% compared to pure TiO₂ (49% and 10%, respectively). Moreover, the photocatalytic activity of pure TiO₂ also showed an improvement with an increase of calcination temperature due to the formation of more anatase phase. This result indicated that the resulting photocatalyst composites might have higher crystallinity of TiO₂ due to the effect of calcination temperature [15].

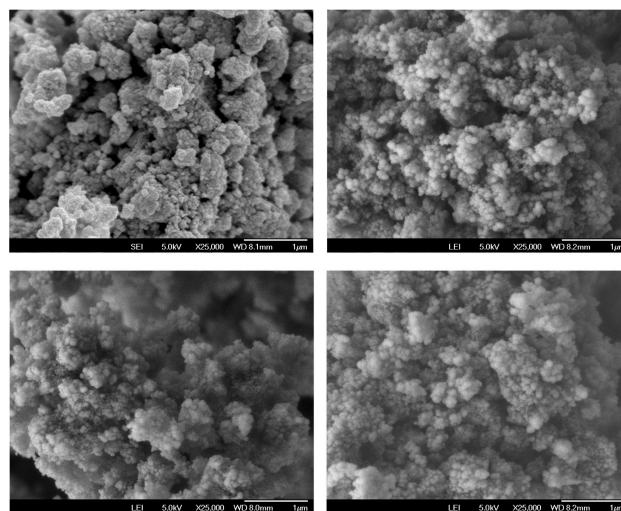


Figure 3. FE-SEM image for the morphology of a) TiO₂ and b-d) [Cu₃Pz₃]/TiO₂ at different calcination temperatures of b) 373, c) 473 and d) 573 K.

Based on photocatalytic of TiO₂, it was expected that the composites gave high activity due to the effect of calcination temperature on the crystallinity of TiO₂. Surprisingly, [Cu₃Pz₃]/TiO₂ composites showed opposite results where the activity slightly decreased after calcined at 473 and 573 K. These results might be due to the decomposition of [Cu₃Pz₃] at high temperature [17]. Hence, presence of [Cu₃Pz₃] for delaying electron-hole recombination by trapping the transferred electrons with its columnar assembly [13,14] and

suitable calcination temperature [15] play an important role for improving photocatalytic activity of pure TiO₂.

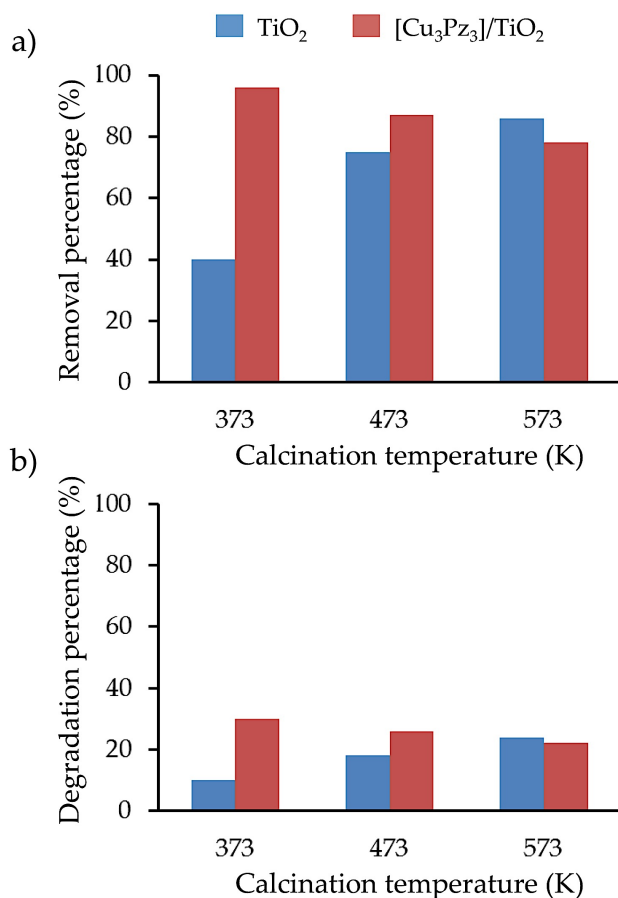


Figure 4. a) Removal and b) degradation percentage of TiO₂ and [Cu₃Pz₃]/TiO₂ at different calcination temperatures.

Conclusions


In conclusion, TiO₂ and [Cu₃Pz₃]/TiO₂ photocatalyst composites were successfully prepared at different calcination temperature (373, 473, and 573 K) by using simple an impregnation method. High calcination temperature slightly affects the crystallite size of pure TiO₂. In contrast, the morphology and crystallite size of [Cu₃Pz₃]/TiO₂ photocatalyst composites were not much affected. Both removal and degradation percentage of 2,4-D for pure TiO₂ increased from 49% to 86% and 10% to 24% when the calcination temperatures were increased from 373 to 473 K and 373 to 573 K. [Cu₃Pz₃]/TiO₂ photocatalyst composite calcined at 373 K showed the highest removal and degradation of 2,4-D compared to other photocatalyst composites with 96% and 30%. In contrast, as the calcination temperature increased, the activity of [Cu₃Pz₃]/TiO₂ photocatalyst composites decreased. This work demonstrated that modification of TiO₂ with metal

complex and suitable calcination temperature might play an important role to enhance the degradation of organic pollutants.

References

- [1] C.J. Burns, and G. M. H. Swaen, Review of 2,4-Dichlorophenoxyacetic Acid (2,4-D) Biomonitoring and Epidemiology, *Crit. Rev. Toxicol.*, **2012**, 42:9, 768-786, DOI: 10.3109/10408444.2012.710576.
- [2] S.Z. Cohen, C. Eiden, and M. N. Lorber, Evaluation of Pesticide in Groundwater, *ACS Symp. Ser. 315, Am. Chem. Soc.*, **1986**, 170-196, DOI: 10.1021/bk-1986-0315.ch010.
- [3] Y.-F. Chao, P.-C. Chen, and S.-L. Wang, Adsorption of 2,4-D on Mg/AL-NO₃ Layered Double Hydroxides with Varying Layer Charge Density, *Appl. Clay Sci.*, **2008**, 40:1-4, 193-200, DOI: 10.1016/j.clay.2007.09.003.
- [4] J. L. Zhang, z. P. Cao, H. W. Zhang, L. M. Zhao, X. D. Sun, and F. Mei, Degradation Characteristics of 2,4-Dichlorophenoxyacetic Acid in Electrobiological System, *J. Hazard. Mater.*, **2013**, 262, 137-142, DOI: 10.1016/j.jhazmat.2013.08.038.
- [5] C. Y. Kwan and W. Chu, A Study of the Reaction Mechanisms of the Degradation of 2,4-Dichlorophenoxyacetic Acid by Oxalate-mediated Photooxidation, *Wat. Res.*, **2004**, 38:19, 4213-4221, DOI: 10.1016/j.watres.2004.06.033.
- [6] A. Fujishima, X. Zhang, and D. A. Tryk, TiO₂ Photocatalysis and Related Surface Phenomena, *Surf. Sci. Rep.*, **2008**, 63, 515-582, DOI: 10.1016/j.surfrep.2008.10.001.
- [7] W. Choi, Pure and Modified TiO₂ Photocatalysts and their Environmental Applications, *Catal Surv. Asia*, **2006**, 10, 16-28, DOI: 10.1007/s10563-006-9000-2.
- [8] M. R. Hoffmann, S. T. Martin, W. Choi, and D. W. Bahnemann, Environmental Applications of Semiconductor Photocatalysis, *Chem. Rev.*, **1995**, 95, 69-96, DOI: 10.1021/cr00033a004.
- [9] A. D. Paola, G. Marci, L. Palmisano, M. Schiavello, K. Uosaki, S. Ikeda, and B. Ohtani, Preparation of Polycrystalline TiO₂ Photocatalysts Impregnated with Various Transition Metal Ions: Characterization and Photocatalytic Activity for the Degradation of 4-Nitrophenol, *J. Phys. Chem. B*, **2001**, 106, 637-645, DOI: 10.1021/jp013074l.
- [10] D. Dvoranova, V. Brezova, M. Mazur, and M. A. Malati, Investigation of Metal-doped Titanium Dioxide Photocatalysts, *Appl. Catal. B: Environ.*, **2002**, 37:2, 91-105, DOI: 10.1016/S0926-3373(01)00335-6.
- [11] C. M. Teh, and A. R. A. Mohamed, Roles of Titanium Dioxide and Ion-doped Titanium Dioxide on Photocatalytic Degradation of Organic Pollutants (Phenolic Compounds and Dyes) in Aqueous Solution: A Review, *J. Alloys and Comp.*, **2011**, 509:5, 1648-1660, DOI: 10.1016/j.jallcom.2010.10.181.
- [12] Y. Tang, S. Luo, Y. Teng, C. Liu, X. Xu, X. Zhang, and L. Chen, Efficient Removal of Herbicide 2,4-Dichlorophenoxyacetic Acid from Water using

- AG/reduced Graphene Oxide Co-decorated TiO₂ Nanotube Arrays, *J. Hazard. Mater.*, **2012**, 241-242, 323-330, DOI: 10.1016/j.jhazmat.2012.09.050.
- [13] H. O. Lintang, N. A. Roslan, N. Ramlan, M. Shamsuddin, and L. Yuliati, Photocatalyst Composites of Luminescent Trinuclear Copper(I) Pyrazolate Complexes/Titanium Oxide for Degradation of 2,4-Dichlorophenoxyacetic Acid, *Mater. Sci. Forum*, **2016**, 846, 697-701, DOI: 10.4028/www.scientific.net/MSF.846.697.
- [14] H. O. Lintang, N. H. Sabran, S. L. Ling, and L. Yuliati, Luminescent Group 11 3,5-Dimethylpyrazolate Complexes/Titanium Oxide Composites for Photocatalytic Removal and Degradation of 2,4-Dichlorophenoxyacetic Acid, *Mater. Res. Express*, **2019**, 6, 064001, DOI: 10.1088/2053-1591/ab058e.
- [15] W. R. Siah, H. O. Lintang, M. Shamsuddin, and L. Yuliati, Effect of Calcination Temperatures on the Photocatalytic Activities of Commercial Titania Nanoparticles under Solar Simulator Irradiation, *Malaysian J. Anal. Sci.*, **2015**, 11:3, 106-110, DOI: 10.11113/mjfas.v11n3.377.
- [16] H. O. Lintang, N. F. Ghazalli, and L. Yuliati, Supramolecular Phosphorescent Trinuclear Copper(I) Pyrazolate Complexes for Vaporchromic Chemosensors of Ethanol, *Indones. J Chem.*, **2017**, 17:2, 191-202, DOI: 10.22146/ijc.22553.
- [17] N. F. Ghazalli, L. Yuliati, S. Endud, M. Shamsuddin, and H. O. Lintang, Vapochromic Copper(I) Pyrazolate Complex Materials for Phosphorescent Chemosensors of Ethanol, *Adv. Mater. Res.*, **2014**, 907, 44-47, DOI: 10.4028/www.scientific.net/AMR.970.44.
- [18] H. V. R. Dias, H. V. K. Diyabalanage, M. G. Eldabaja, O. Elbjairami, M. A. R. Omary, and M. A. Omary, Brightly Phosphorescent Trinuclear Copper(I) Complexes of Pyrazolates: Substituent Effects on Supramolecular Structure and Photophysics, *J. Am. Chem. Soc.*, **2005**, 127, 7480-7501, DOI: 10.1021/ja0427146.
- [19] W. R. Siah, H. O. Lintang, M. Shamsuddin, and L. Yuliati, High Photocatalytic Activity of Mixed Anatase-rutile Phase on Commercial TiO₂ Nanoparticles, *IOP Conf. Ser. Mat. Sci. Eng.*, **2016**, 107, 012005, DOI: 10.1088/1757-899X/107/1/012005.
- [20] L. Yuliati, W. R. Siah, N. A. Roslan, M. Shamsuddin, and H. O. Lintang, Modification of Titanium Dioxide Nanoparticles with Copper Oxide Co-catalyst for Photocatalytic Degradation of 2,4-Dichlorophenoxyacetic Acid, *Malaysian, J. Anal. Sci.*, **2016**, 20, 171-178, DOI: 10.17576/mjas-2016-2001-18.
- [21] P. Praveen, G. Viruthagiri, S. Mugundan, and N. Shanmugan, Structural, Optical and Morphological Analyses of Pristine Titanium Dioxide Nanoparticles-synthesized via Sol-gel Route, *Spectrochim. Acta A.*, **2014**, 117, 622-629, DOI: 10.1016/j.saa.2013.09.037.
- [22] W. R. Siah, H. O. Lintang, M. Shamsuddin, H. Yoshida, and L. Yuliati, Masking Effect of Copper Oxides Photodeposited on Titanium Dioxide: Exploring UV, Visible, and Solar Light Activity, *Catal. Sci. Tech.*, **2016**, 6, 5079-5087, DOI: 10.1039/c6cy00074f.

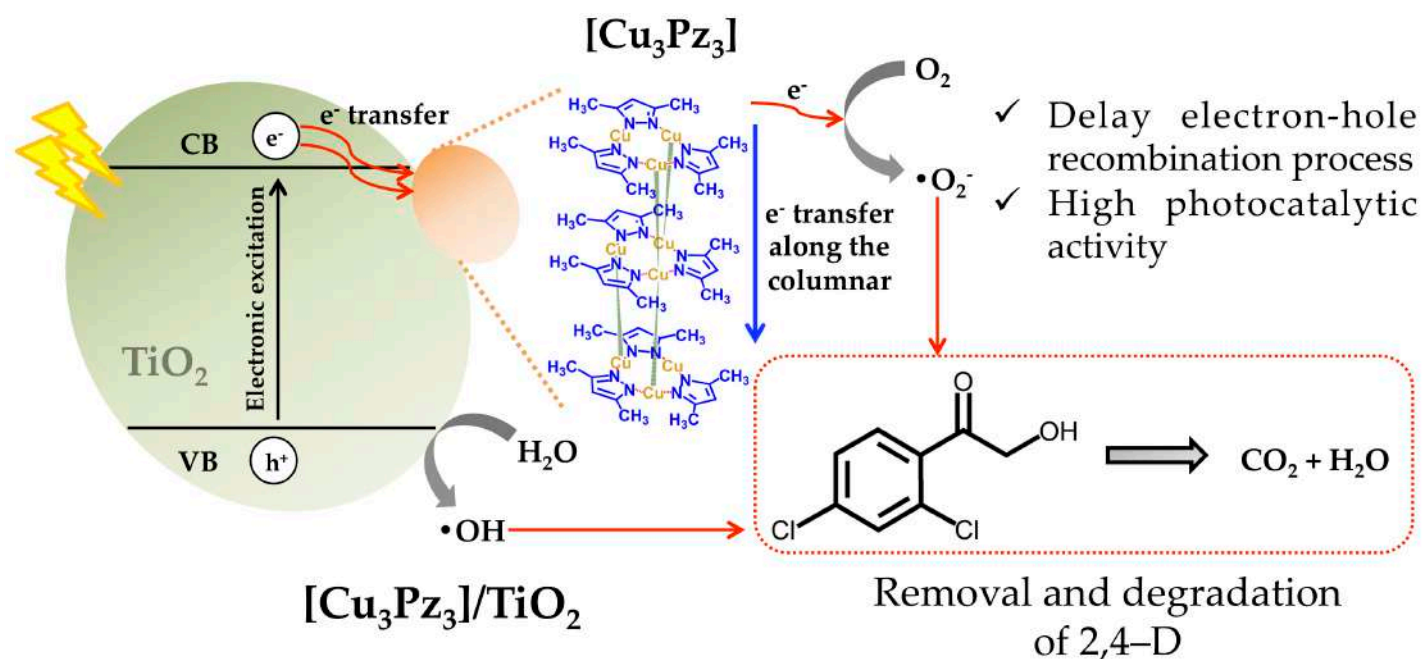

Sabran *et al.* on page 54 with DOI number of 10.34311/jics.2019.02.1.54 entitled "**Systematic Study of Calcination Temperature on Photocatalytic Activity of Luminescent Copper(I) Pyrazolate Complex/Titanium Oxide Composites**" have been selected as a cover picture.

In this report, luminescent composites $[\text{Cu}_3\text{Pz}_3]/\text{TiO}_2$ enable as a semiconductor photocatalyst with a significant improvement on photocatalytic activity for removal and degradation of 2,4-D. This higher photocatalytic activity compared to TiO_2 is due to the presence of columnar assembly for delaying electron-hole recombination between valance and conduction bands. Indeed, calcination temperature is important parameter to increase photocatalytic activity of photocatalyst

Indonesian Chemical Society (ICS) of Himpunan Kimia Indonesia (HKI) has decided to start again its flagship publication through Journal of the Indonesian Chemical Society (J. Idn. Chem. Soc. or JICS) and Proceeding of the Indonesian Chemical Society (Proc. Idn. Chem. Soc. or PICS). Since the first volume and issue of JICS on April 2006 for the printed version, other volumes have not yet been published again so far. Hence, JICS and PICS have been decided to be published again through the electronic version with the web address of <https://journal.hki.or.id>.

JICS with web address of <https://journal.hki.or.id/JICS> is the flagship international e-journal for publication of any scientific articles as **recent research progress, review, mini review, full paper and communication**, consisting all aspects of chemistry fields or chemical sciences with high originality and impact through out a double-blind peer-review process. JICS will publish **three issues annually in April, August and December** with a free "Article Processing Charge". In order to enhance publication, JICS involve editorial teams consisting of editor-in-chief, vice editor-in-chief, journal manager, managing editors, section editors, national and international advisory editors, copyeditors, layout editors, and administration support. It is expected that JICS will be a good journal in chemistry fields or chemical sciences.

The second volume and first issue in August 2019 provides **7 articles** consisting of **1 recent research progress, 1 review, 1 mini review, 3 full papers and 1 communication**. It involves authorships from **6 countries such as Indonesia, Malaysia, Japan, India, Taiwan and Nigeria**. All peer-reviews are performed in double blind process that used 2 reviewers from different institutions for evaluation of each manuscript after completed the first assessment by the Editor-in-Chief or Vice Editor-in-Chief in the plagiarism check (similarity index using Turnitin). Upon accepted, the manuscript will follow the copyedited by copyeditors and then layout edited by layout editors for the production process. Moreover, each published article will be indexed in Google Scholar and it will have DOI number with specific prefix.

With this JICS publication, it will contribute to the advancement of chemical sciences in Indonesia and in the region.

Malang, 31 August 2019
Hendrik Oktendy Lintang

JICS Editor-in-Chief

**J. Idn. Chem. Soc. 2019, Volume 02, Issue 1
31 August 2019**


Recent Research Progress

Recent Advances in Injectable Hydrogels for Biomedical Applications 1-6

*Eko Adi Prasetyanto**

Department of Pharmacy, Faculty of Medicine and Health Sciences,
Atma Jaya Catholic University of Indonesia, Indonesia

J. Idn. Chem. Soc. 2019, 02(1), 1-6 , DOI: 10.34311/jics.2019.02.1.1

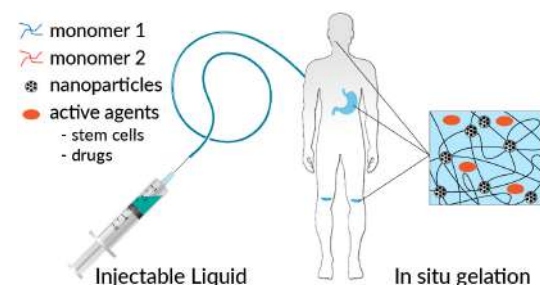

Hydrogel is one of the best 3D scaffold materials and become a trending research field in the area of regenerative medicine and tissue/bone engineering. In this manuscript, author describes recent development in the area of Injectable Hydrogels. Compared to other reports, this article distinctively focuses on the general requirements to synthesize an ideal injectable hydrogel for biomedical applications.


Review

Microfluidics Era in Chemistry Field: A Review 7-23

Yehezkiel Steven Kurniawan, Arif Cahyo Imawan, Sathuluri Ramachandra Rao, Keisuke Ohto, Wataru Iwasaki, Masaya Miyazaki, and Jumina*

Ma Chung Research Center for Photosynthetic Pigments,
Universitas Ma Chung, Indonesia

J. Idn. Chem. Soc. 2019, 02(1), 7-23 , DOI: 10.34311/jics.2019.02.1.7

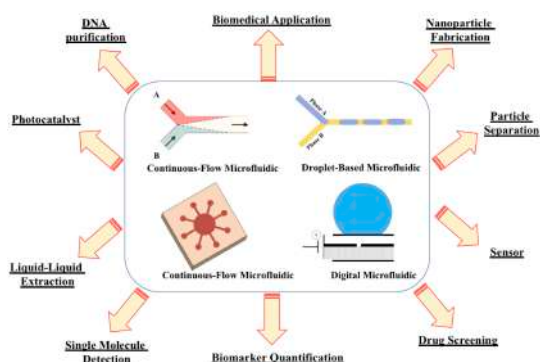

Microfluidic field has been thoroughly investigated and applied for chemistry field, especially for separation, purification, qualitative and quantitative analysis, and biomedical field.

TABLE OF CONTENTS


Mini-Review

On the Renewable Polymers from Agro-industrial Biomass: A Mini-Review 24-41

Roswanira Abdul Wahab*, Jacob Adikwu Gowon, and Nursyafiqah Elias

Department of Chemistry, Faculty of Science,
Universiti Teknologi Malaysia, Malaysia

J. Idn. Chem. Soc. 2019, 02(1), 24-41 , DOI: 10.34311/jics.2019.02.1.24

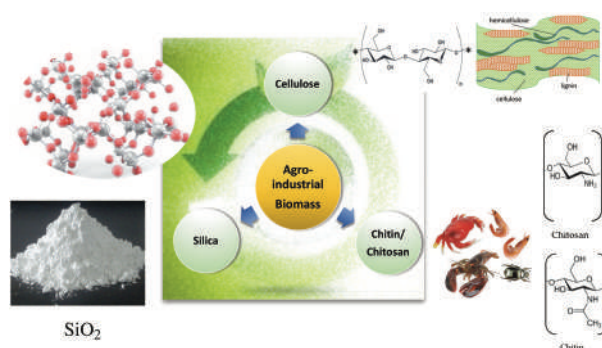

This mini review highlights the potential use of renewable polymers obtained from agro-industrial biomass. Three major natural polymers are discussed, namely the organic-based biomass cellulose and chitin/chitosan, as well as the inorganic, silica (SiO₂). This is followed by discussions on sources of these natural polymers, including techniques of their isolation and purification, as well as the current applications of the cellulosic, chitin and biogenic silica-based composites.

Full Papers

Antibacterial and Biofilm Degradation Activity of Extract from Steam 42-47

Distillation Residue of Zingiberaceae Leaves Against *Streptococcus mutans*

Irmanida Batubara*, Dian Yunita, and Irma Herawati Suparto

Department of Chemistry, Faculty of Mathematic and Natural Sciences,
IPB University, Indonesia

J. Idn. Chem. Soc. 2019, 02(1), 42-47 , DOI: 10.34311/jics.2019.02.1.42



Extract from the steam distillation residue of Zingiberaceae leaves was used as antibacterial and biofilm degradation agent against *Streptococcus mutans* using microdilution technique. The methanol extract of *C. zedoaria* leaves shows the highest antibacterial activity with MIC and MIB values of 15.63 ppm and the best to degrade the biofilm with inhibitory concentration 50% (IC₅₀) of 15.33 ppm.


TABLE OF CONTENTS

Synthesis and Characterization of Activated Carbon from Sago Waste (Metroxylon sagu) with ZnCl₂ Activation and HNO₃ Modification 48-53

Yanti Kiding Allo, Sudarmono, and Octolia Togibasa*

Department of Physics, Faculty of Mathematics and Natural Sciences, Universitas Cenderawasih Jayapura, Indonesia

J. Idn. Chem. Soc. **2019**, 02(1), 48-53 , DOI: 10.34311/jics.2019.02.1.48

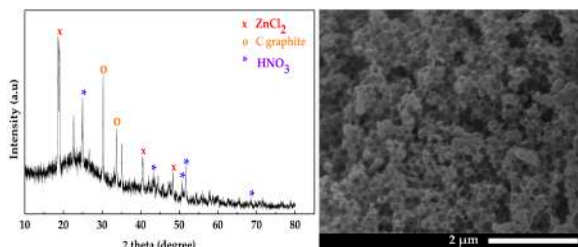


From the series of processes of carbonization, extraction, activation with ZnCl₂, and modification using 1.5 mL of HNO₃ of lignocellulose contained in sago waste, it provides the modified-activated carbon samples with XRD pattern (left) for exfoliated graphite crystals. Moreover, SEM image (right) for this sample shows nanoporous particles with regular homogeneous shapes in the range of 200 nm in size.

Systematic Study of Calcination Temperature on Photocatalytic Activity of Luminescent Copper(I) Pyrazolate Complex/Titanium Oxide Composites 54-59

Nurul Husna Sabran, Leny Yuliati, Siew Ling Lee, and Hendrik O. Lintang*

Department of Chemistry, Faculty of Science and Technology, Universitas Ma Chung, Indonesia

J. Idn. Chem. Soc. **2019**, 02(1), 54-59 , DOI: 10.34311/jics.2019.02.1.54

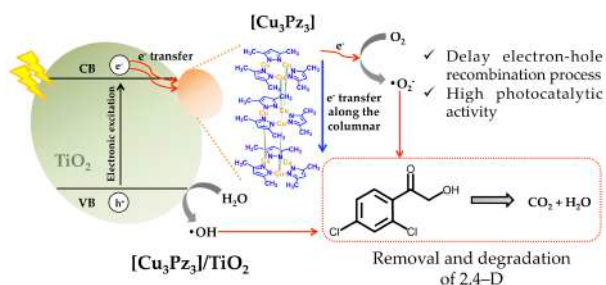

Luminescent composites [Cu₃Pz₃]/TiO₂ enable as a semiconductor photocatalyst with a significant improvement on photocatalytic activity for removal and degradation of 2,4-D. This higher photocatalytic activity compared to TiO₂ is due to the presence of columnar assembly for delaying electron-hole recombination between valance and conduction bands. Indeed, calcination temperature is important parameter to increase photocatalytic activity of photocatalyst composites.


TABLE OF CONTENTS

Communication

Application of Lecithin-templated Mesoporous Silica Microparticles for the Specific and Selective Removal of Phospholipids 60-65

David Marikah, Lee Wah Lim*, and Toyohide Takeuchi

J. Idn. Chem. Soc. 2019, 02(1), 60-65 , DOI: 10.34311/jics.2019.02.1.60

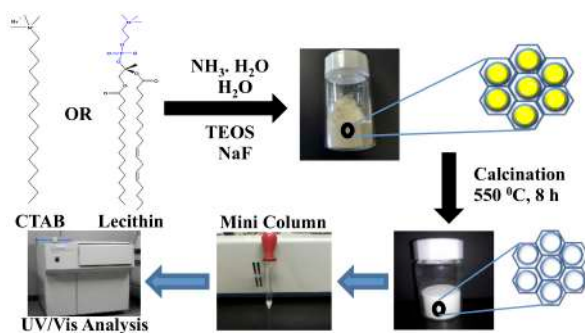

Lecithin was used as the template, in comparison to the conventional cetyltrimmonium salts (CTAB was used in this study), in synthesizing mesoporous silica microparticles for the selective adsorption of phospholipids. The synthesized materials revealed good textural and porosity properties, which found to be effective in dictating the phospholipids quantities adsorbed during the column breakthrough studies.